



*Citation for published version:*

Walsh, D, Sanchez-Ballester, NM, Ting, VP, Ariga, K & Weller, MT 2016, 'Visible light promoted photocatalytic water oxidation: proton and electron collection: via a reversible redox dye mediator', *Catalysis Science and Technology*, vol. 6, no. 11, pp. 3718-3722. <https://doi.org/10.1039/c6cy00139d>

*DOI:*

[10.1039/c6cy00139d](https://doi.org/10.1039/c6cy00139d)

*Publication date:*

2016

*Document Version*

Peer reviewed version

[Link to publication](#)

The final publication is available at the Royal Society of Chemistry via [10.1039/c6cy00139d](https://doi.org/10.1039/c6cy00139d)

**University of Bath**

**Alternative formats**

If you require this document in an alternative format, please contact:  
[openaccess@bath.ac.uk](mailto:openaccess@bath.ac.uk)

**General rights**

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

**Take down policy**

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

# Visible light promoted photocatalytic water oxidation: proton and electron collection via reversible redox dye mediator

Dominic Walsh,<sup>\*a</sup> Noelia M. Sanchez-Ballester,<sup>b</sup> Valeska P. Ting,<sup>c</sup> Katsuhiko Ariga,<sup>d</sup> and Mark T. Weller<sup>\*</sup>

**Visible light promoted photocatalytic water oxidations were conducted using a homogenous cobalt complex as a catalyst that was absorbed onto a silica gel substrate. The porous SiO<sub>2</sub> contained Ru(bpy)<sub>3</sub><sup>2+</sup> as light harvester and the redox quinone analogue DCPIP as a reversible electron mediator as a step towards utilization of protons and electrons liberated in water oxidations for solar fuels.**

Sunlight is probably the leading alternative energy source available being plentiful, inexhaustible and safe. However electricity cannot be stored on the scale required and routes to solar fuels such as H<sub>2</sub> and methanol need to be developed using materials and methods applicable on a large scale.<sup>1-3</sup> In natural photosynthesis an inorganic CaMn<sub>4</sub>O<sub>5</sub> arrangement evolved as a catalyst for the oxidation of water into gaseous O<sub>2</sub> and protons.<sup>4</sup> This ubiquitous cluster is housed within an elaborate supporting and regenerating oxygen evolving centre (OEC), itself contained within the plant chloroplast PSII complex. But it is worth noting that the manganese based structure may have evolved from a more primitive photosystem and that there are other metals equivalent or superior to manganese for the catalytic role that can be used in artificial systems. The artificial photocatalytic water oxidation reaction comprises (a) visible light, (b) a chemical light harvester, (b) a catalyst for dissociation of water molecules and (c) a sacrificial redox agent. For practical application many improvements need to be made in terms of efficiency, cost and toxicity of the reaction.<sup>5</sup>

The use of persulfate use as sacrificial electron acceptor has persisted since outset of studies of photocatalyzed water oxidations in the 1980s; however the powerful sulphate anion radical is generated which decomposes organics, generates CO<sub>2</sub> and limits reaction lifetime. A pentamine cobalt complex acceptor has also been employed widely, however this was demonstrated in our previous work and in the literature as potentially acting as a secondary catalyst following conversion *in-situ*.<sup>6-8</sup> Whilst catalyst and electron acceptor working in tandem can improve yields, the ultimate aim is to dispense with irreversible electron acceptors and utilize the protons and electrons for reductions into fuels. The use of an alternate electron mediator has clear benefits in developing this technology. Here we report the use of the redox quinone analogue 2,6-dichlorophenoinodophenol (DCPIP) as a reversible electron mediator for collection of protons and electrons generated in an artificial photocatalyzed water dissociation. The successful viability of using a range of quinones or other agents such as polyamines as an electron collector with Ru(bpy)<sub>3</sub><sup>2+</sup> has been reported.<sup>9-11</sup>

Under basic conditions DCPIP has an intense blue colouration (Abs λ<sub>max</sub> = 590nm) which converts to colourless upon reduction and protonation (Fig. 1 and ESI † Fig. S1). The Hill reaction using extracts from plant leaves has utilized this

reagent extensively,<sup>12, 13</sup> however its use in fully artificial water oxidations systems has not been investigated. Here the DCPIP plays an equivalent role to NADP<sup>+</sup>.<sup>14, 15</sup> Partially reduced DCPIPH is pink, further reduction gives colourless DCPIPH<sub>2</sub> which is equivalent to NADPH+H<sup>+</sup> produced by light dependant photosynthesis PSII/PSI and can potentially be used as a synthetic proton/electron storage molecule.




Fig. 1 The redox indicator DCPIP (as sodium salt) is able to reversibly accept 2 protons and 2 electrons to form DCPIPH<sub>2</sub>, onset of loss of the intense blue colouration occurs at ~pH 6.5 with formation of reduced pink DCPIPH then colourless DCPIPH<sub>2</sub>.

Ru(bpy)<sub>3</sub><sup>2+</sup> and DCPIP can be incorporated into silica sol-gels which facilitates its recovery and re-use in reactions (see ESI for experimental details).<sup>16</sup> BET measurements of lightly ground samples gave a surface area of ~348m<sup>2</sup>/g (BJH average pore diameter of ~41Å), the isotherm plot consistent with a micro/mesoporous material is shown in ESI† Fig. S2.

A soluble cobalt hydroxide-amino complex as catalyst was developed as a homogeneous catalyst to optimize interaction between the supported reagents. TGA and DTA analysis showed the sample was largely decomposed upon heating to 320°C, a partially reduced CoO/Co residue was formed. Residual mass after removal of absorbed water was ~40wt%. This is consistent with a Co(OH)<sub>x</sub>(NH<sub>3</sub>)<sub>(6-x)</sub> sample (ESI† Fig. S3). FT-IR analysis showed strong absorption bands at 655cm<sup>-1</sup> due to Co-OH vibrations and weak Co-NH<sub>3</sub>(sym) deformation bands at 1340 and 1400 together with water OH bands at 1630 and 3375cm<sup>-1</sup> (ESI† Fig. S4).<sup>17</sup> This suggests the six-coordinate Co is primarily ligated by OH with minimal NH<sub>3</sub>. In previous work more elaborate cobalt complexes were able to catalyse photo-oxidations.<sup>6</sup>

Stirred photocatalytic water oxidations were illuminated with a 3W blue LED (λ<sub>max</sub> 465 nm) held at a calibrated distance such that light intensity at the flask surface was 5mWcm<sup>-2</sup>. Initial evaluations of the soluble cobalt complex catalyst activity were undertaken using a standard procedure with [Ru(bpy)<sub>3</sub>Cl]<sub>2</sub> sensitizer (MLCT absorbance maximum λ<sub>453nm</sub>) and [Co(NH<sub>3</sub>)<sub>5</sub>Cl] as electron acceptor in N<sub>2</sub> degassed DI acetate buffer at pH 5.2. For reactions utilizing the reversible electron mediator, 2.5g of lightly ground SiO<sub>2</sub> containing the Ru(bpy)<sub>3</sub><sup>2+</sup> sensitizer and DCPIP together with cobalt complex added in solution and of N<sub>2</sub> degassed DI water with pH adjusted to 7.2 with dilute NH<sub>4</sub>OH was used. Following one reaction the SiO<sub>2</sub> gel powder was retrieved by filtration, washed, carefully degassed and DCPIP regenerated in highly dilute degassed

ammonia at pH 7.2 before reuse. The release of O<sub>2</sub> and reaction mixture pH were monitored simultaneously in situ and in real time. An optical O<sub>2</sub> sensor combined with a temperature compensation probe was used for accurate measurement of gaseous O<sub>2</sub> released into the headspace (full experimental details are described in the ESI<sup>†</sup>).

#### Photocatalytic water oxidations using cobalt complex

Standard reactions to test activity of the soluble cobalt hydroxide complex as a homogenous catalyst showed that a total of ~90 μmol of O<sub>2</sub> was evolved after 75 min of reaction time. This gives an efficiency of 75% based on a maximum yield of 120 μmol due to electron acceptor concentration.<sup>6</sup> pH of the system rose from 5.2 up to 8.5 due to gradual decomposition of electron acceptor and generation of ammonia upon electron capture from the excited state Ru(bpy)<sub>3</sub><sup>2+\*</sup>.<sup>18</sup> The pentamine electron acceptor itself can contribute to O<sub>2</sub> and proton generation due to in-situ conversion into cobalt oxide.<sup>6-7</sup> This process was believed to become significant after approximately 40 min reaction time and may account for the upswing in O<sub>2</sub> generation at around this point. This suggests O<sub>2</sub> evolved solely due to conversion of the cobalt complex to active Co<sup>3+</sup> was ~60 μmol (Fig. 2a,b), the additional O<sub>2</sub> being generated from cobalt oxide derived from both cobalt complexes.

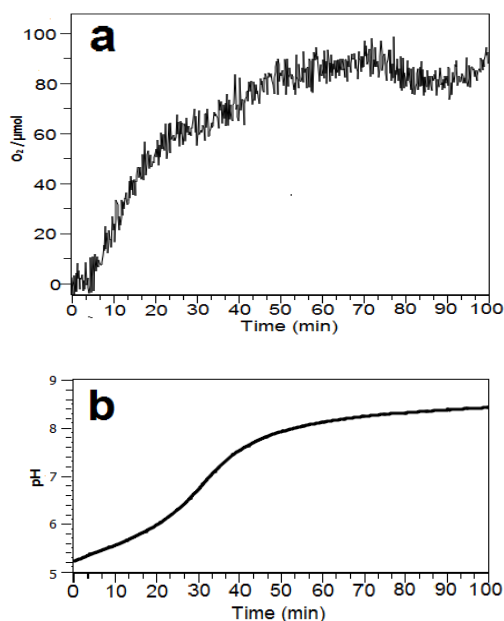


Fig. 2 (a) Visible light photocatalysed water oxidations showing O<sub>2</sub> yield with time using 5mWcm<sup>-2</sup> blue light using 20mg of prepared Co(OH)(NH<sub>3</sub>) complex as homogeneous catalyst; (b) change in pH of the reaction mixture with time.

#### Photocatalytic reactions using DCPIP as electron mediator

Reactions using DCPIP in solution resulted in no measurable O<sub>2</sub> generation, presumably due to the intense deep blue coloured DCPIP blocking most incoming light. Also sol gels prepared incorporating Ru(bpy)<sub>3</sub><sup>2+</sup>, DCPIP and soluble cobalt complex catalyst and were not active. However activity was obtained when the cobalt complex was firstly absorbed in a stirred photo reaction onto SiO<sub>2</sub>-DCPIP-Ru(bpy)<sub>3</sub><sup>2+</sup> gels and then a further

photocatalytic reaction undertaken using the recovered and washed combined SiO<sub>2</sub>/Ru(bpy)<sub>3</sub><sup>2+</sup>/DCPIP/Co<sup>2+/3+</sup> gel composite. Fig. 3 shows evolution of O<sub>2</sub> after light-on using this in-situ generated silica supported reagent mixture. It is worth noting that prior careful degassing to remove air from the combined SiO<sub>2</sub> microporous gel, which would otherwise quench the light generated Ru(bpy)<sub>3</sub><sup>2+\*</sup> state, was required for its successful use in the photocatalytic reactions (see ESI<sup>†</sup> for experimental details).

After 30 min of reaction a maximum O<sub>2</sub> yield of ~54 μmol was obtained. Activity and reaction lifetime was reduced compared to the homogeneous catalysed system, in part because of the absence of the pentamine electron acceptor conversion to active catalyst during later stages of the reaction. The SiO<sub>2</sub> gel with incorporated reagents was then recovered by filtration, washed and degassed and used in a further photocatalytic reaction. After 30 min a reduced O<sub>2</sub> yield of ~38 μmol of O<sub>2</sub> was obtained. The reduction in activity of the silica gel supported mixture was probably due to degradation and some leaching of reagents into the reaction solution. The measured pH of the reaction mixtures remained almost unchanged, indicating collection of protons by the DCPIP.

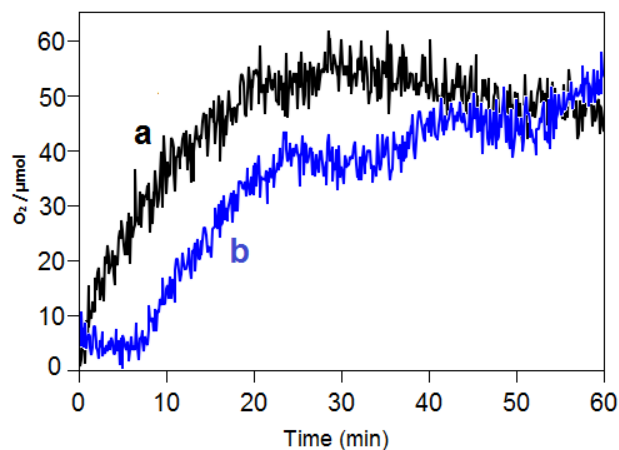


Fig.3 Visible light photocatalysed water oxidations showing O<sub>2</sub> yield with time using 5mWcm<sup>-2</sup> blue light with (a) SiO<sub>2</sub> support containing Ru(bpy)<sub>3</sub><sup>2+</sup> and DCPIP with cobalt complex post absorbed; (b) repeat reaction using recovered, washed and degassed SiO<sub>2</sub> support with its incorporated reagents.

Furthermore, it was observed that the SiO<sub>2</sub>-DCPIP-Ru(bpy)<sub>3</sub><sup>2+</sup> with absorbed cobalt complex changed from a deep blue colour due to oxidized DCPIP into a red/orange colour. This was likely due to formation of reduced DCPIPH and DCPIPH<sub>2</sub> which allowed the red/orange colour of this, the Ru(bpy)<sub>3</sub><sup>2+</sup> and the cobalt complex to become visible (Fig. 4).

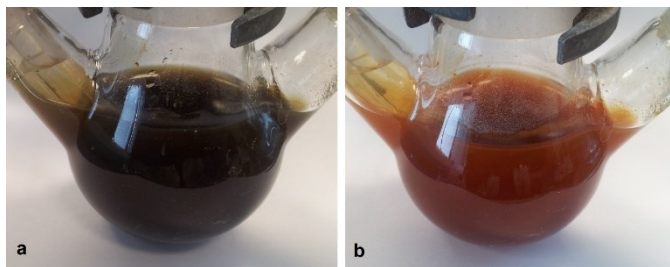


Fig. 4 Images of photocatalytic water oxidation reaction mixture using SiO<sub>2</sub> gel containing both Ru(bpy)<sub>3</sub> and DCPIP and Co complex in solution; (a) reaction mixture before exposure to blue LED light; (b) after exposure to the blue LED light for 100 min.

XPS analysis was used to determine the elemental composition of the catalyst, this showed the presence of Ru and also Co in SiO<sub>2</sub> support (ESI<sup>+</sup> Fig. S5). The Co 2p binding energy region showed the presence of mainly Co<sup>2+</sup>, with 2p<sub>3/2</sub> and 2p<sub>1/2</sub> bands at 782 and 798eV respectively. A 3d-4s shake up was present at 787eV, also a small satellite peak situated at ~790eV was indicative of a low level of Co<sup>3+</sup> due to Co<sub>3</sub>O<sub>4</sub> (Fig. 5).<sup>19-21</sup>

Table 1 shows the composition of the generated SiO<sub>2</sub> catalyst mixture as measured by XPS. This showed that 2.5g of ground material had ~25mg of absorbed Co(OH)<sub>2</sub>/Co<sub>3</sub>O<sub>4</sub> and contained ~50mg of [Ru(bpy)<sub>3</sub>Cl]<sub>2</sub>, though not all of this would be accessible for reaction.

A simple further test using a solution of 20% hydrogen peroxide to confirm presence of cobalt ions was conducted.

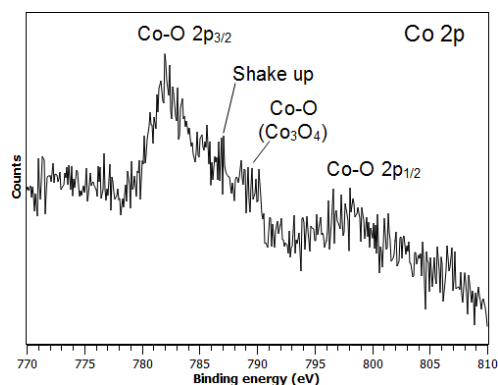


Fig. 5 High resolution XPS analysis of a washed sample of SiO<sub>2</sub>/Ru(bpy)<sub>3</sub><sup>2+</sup>/DCPIP following a photocatalytic reaction with homogeneous cobalt complex as catalyst. The Co2p region has band position and shape consistent with Co<sup>2+</sup> together with small bands consistent with cobalt oxide as Co<sub>3</sub>O<sub>4</sub>. This shows the cobalt complex was adsorbed onto the SiO<sub>2</sub> support and partly oxidized in-situ.

Ground SiO<sub>2</sub> prepared with Ru(bpy)<sub>3</sub><sup>2+</sup> and DCPIP showed no reaction upon addition to H<sub>2</sub>O<sub>2</sub> solution. Significantly however, rapid and abundant H<sub>2</sub>O<sub>2</sub> decomposition with generation of O<sub>2</sub> bubbles occurred with a washed SiO<sub>2</sub>/Ru(bpy)<sub>3</sub><sup>2+</sup>/DCPIP retrieved following a photocatalytic reaction with cobalt complex in solution as catalyst.

Table 1 XPS analysis showing measured atomic and weight % of elements present in washed sample of SiO<sub>2</sub>/Ru(bpy)<sub>3</sub><sup>2+</sup>/DCPIP obtained following a photocatalytic reaction using the soluble cobalt complex as catalyst.

Element	At% (Wt%)	Element	At% (Wt%)
C	4.8 (3.03)	Cl	0.1 (0.19)
N	0.4 (0.29)	Co	0.2 (0.62)
O	68.79 (57.77)	Ru	0.05 (0.27)
Si	25.66 (37.83)		

Fluorescence resulting from relaxation of electrons from the MLCT Ru(bpy)<sub>3</sub><sup>2+</sup>\* excited state via intersystem crossing to a triplet state and subsequent Stokes shifted emission to ground state in the silica support samples was examined by illumination of the powder samples by blue led light. Fig. 6 and shows the emission at ~600nm from samples containing Ru(bpy)<sub>3</sub>. Samples recovered after photocatalysis showed reduced fluorescence intensity, probably due to some leaching. Typical absorption/fluorescence wavelengths were measured (ESI<sup>+</sup> Fig. S6).<sup>22</sup>



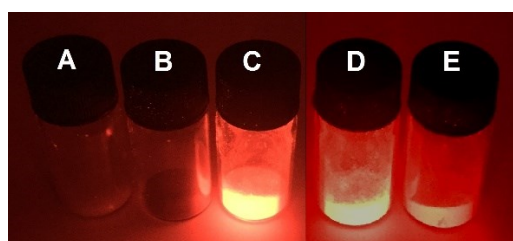


Fig. 6 Image of silica samples showing (a) SiO<sub>2</sub> only; (b) SiO<sub>2</sub>-DCPIP; (c) SiO<sub>2</sub>-Ru(bpy)<sub>3</sub><sup>2+</sup>; (d) SiO<sub>2</sub>-Ru(bpy)<sub>3</sub><sup>2+</sup>-DCPIP; (e) SiO<sub>2</sub>-Ru(bpy)<sub>3</sub><sup>2+</sup>-DCPIP after one reaction in presence of Co<sup>2+</sup>. (A blue light filter was used to show the yellow/orange emission).

Overall these results show the cobalt hydroxide-amino complex was adsorbed onto the SiO<sub>2</sub> substrate during the initial stirred photocatalytic reaction. The XPS results suggest some was converted to Co<sub>3</sub>O<sub>4</sub> via excited state Ru(bpy)<sub>3</sub><sup>2+</sup>\* electron extraction from Co<sup>2+</sup> giving Co<sup>3+</sup> without O<sub>2</sub> evolution. Thereafter Co<sup>3+/4+</sup> cycling and water oxidation occurs with generation of O<sub>2</sub> and protons:<sup>6</sup>



The suggested processes involved in water oxidation with the combined silica support are shown in Scheme 1a,b.

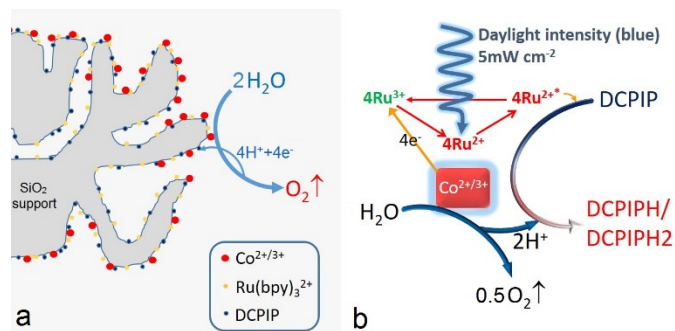

Scheme 1. (a) Microporous silica support containing  $\text{Ru}(\text{bpy})_3^{2+}$  light harvester and DCPIP as electron mediator and proton capture molecule with cobalt catalyst post absorbed to the support surface; (b) photocatalyzed water oxidation processes at silica support surface. Electrons and protons are captured by the DCPIP which is reduced and  $\text{O}_2$  gas by-product liberated.

## Conclusions

These experiments have shown that porous  $\text{SiO}_2$  can be used as a reusable support for the  $\text{Ru}(\text{bpy})_3^{2+}$  light harvester and DCPIP as electron mediator for visible light promoted water oxidations. Degassing of the silica supports and post absorption of cobalt complex to the silica outer surface was found necessary to be a necessary step to avoid likely quenching of the  $\text{Ru}(\text{bpy})_3^{2+*}$  excited state by oxygen in air and generated by the water oxidation. The DCPIP was found to function as an example reversible redox storage molecule and signifies possible future routes to utilization of the electron and protons released by water oxidation for solar fuel production. Further work on utilizing alternative electron mediators and increasing reaction efficiencies is currently underway.

## Acknowledgements

DW and MTW acknowledge funding from a UoB Faculty of Science departmental grant. NSB and KA thank ICS-UoS, NIMS and JSPS for funding. VPT acknowledges funding from a UoB Prize Research Fellowship.

## Notes and references

1. A. Harriman, *European Journal of Inorganic Chemistry*, 2014, **2014**, 573-580.
2. C. Herrero, A. Quaranta, W. Leibl, A. W. Rutherford and A. Aukauloo, *Energy & Environmental Science*, 2011, **4**, 2353-2365.
3. M. Morikawa, Y. Ogura, N. Ahmed, S. Kawamura, G. Mikami, S. Okamoto and Y. Izumi, *Catalysis Science & Technology*, 2014, **4**, 1644-1651.
4. Y. Umena, K. Kawakami, J.-R. Shen and N. Kamiya, *Nature*, 2011, **473**, 55-60.
5. E. Y. Tsui, J. S. Kanady and T. Agapie, *Inorganic Chemistry*, 2013, **52**, 13833-13848.
6. D. Walsh, N. M. Sanchez-Ballester, K. Ariga, A. Tanaka and M. Weller, *Green Chemistry*, 2015, **17**, 982-990.

7. D. Walsh, N. M. Sanchez-Ballester, V. P. Ting, S. R. Hall, L. R. Terry and M. T. Weller, *Catalysis Science & Technology*, 2015, **5**, 4760-4764.
8. D. Hong, J. Jung, J. Park, Y. Yamada, T. Suenobu, Y.-M. Lee, W. Nam and S. Fukuzumi, *Energy & Environmental Science*, 2012, **5**, 7606-7616.
9. J. R. Darwent and K. Kalyanasundaram, *Journal of the Chemical Society, Faraday Transactions 2: Molecular and Chemical Physics*, 1981, **77**, 373-382.
10. J. H. Kim, M. Lee and C. B. Park, *Angewandte Chemie International Edition*, 2014, **53**, 6364-6368.
11. Y. Yasu, T. Koike and M. Akita, *Chemical Communications*, 2012, **48**, 5355-5357.
12. R. Hill, *Proceedings of the Royal Society of London B: Biological Sciences*, 1939, **127**, 192-210.
13. C.A. Goldman, Tested studies for Laboratory Teaching: Proceedings of the Workshop/Conference of the Association for Biology Laboratory Education. Proceedings of the 15<sup>th</sup> Workshop. 1993, Vol 15, New Haven, Connecticut, USA.
14. B. Semin, L. Davletshina, K. Timofeev, I. y. Ivanov, A. Rubin and M. Seibert, *Photosynth Res*, 2013, **117**, 385-399.
15. B. Prieto-Simón and E. Fàbregas, *Biosensors and Bioelectronics*, 2004, **19**, 1131-1138.
16. F. Kopnov, I. Cohen-Ofri and D. Noy, *Angewandte Chemie International Edition*, 2011, **50**, 12347-12350.
17. J. J. Fripiat and J. Helsen, in *Clays and Clay Minerals*, ed. S. W. Bailey, Pergamon, 1966, DOI: <http://dx.doi.org/10.1016/B978-0-08-011908-3.50016-5>, pp. 163-179.
18. L. Duan, Y. Xu, P. Zhang, M. Wang and L. Sun, *Inorganic Chemistry*, 2010, **49**, 209-215.
19. M. C. Biesinger, L. W. M. Lau, A. R. Gerson and R. S. C. Smart, *Applied Surface Science*, 2010, **257**, 887-898.
20. S. C. Petitto and M. A. Langell, *Journal of Vacuum Science & Technology A*, 2004, **22**, 1690-1696.
21. W. Guo, Y. E. I. Gao, L. Fan and S. Yang, *Chemical Communications*, 2010, **46**, 1290-1292.
22. P. Innocenzi, H. Kozuka and T. Yoko, *The Journal of Physical Chemistry B*, 1997, **101**, 2285-2291.