



Citation for published version:

O'Kane, S, Richardson, G, Niemann, R, Foster, J, Cameron, P & Walker, A 2015, 'Parametric study of perovskite solar cells using drift-diffusion modelling', 1st International Conference on Perovskite Solar Cells and Photovoltaics, Lausanne, Switzerland, 27/09/15 - 29/11/16.

Publication date:
2015

Document Version
Publisher's PDF, also known as Version of record

[Link to publication](#)

University of Bath

Alternative formats

If you require this document in an alternative format, please contact:
openaccess@bath.ac.uk

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Parametric study of perovskite solar cells using drift-diffusion modelling

Simon O'Kane¹, Giles Richardson², Ralf Niemann³, Jamie Foster²,
Petra Cameron³ and Alison Walker¹

¹Department of Physics, University of Bath, BA2 7AY, United Kingdom

²Department of Mathematical Sciences, University of Southampton, SO17 1BJ, UK

³Department of Chemistry, University of Bath, BA2 7AY, United Kingdom



UNIVERSITY OF
BATH



University
of Southampton

Contact: S.E.J.O'Kane@bath.ac.uk, G.Richardson@soton.ac.uk, A.B.Walker@bath.ac.uk

Motivation


We have developed a drift-diffusion model of perovskite solar cells that includes the effect of moving ions and is therefore able to predict hysteresis curves similar to those observed in measurements. This model can be used to investigate the effect of different types of ions and different recombination mechanisms.

Conclusions

1. Our drift-diffusion model of perovskite cells with moving ions predicts hysteresis similar to that observed in measurements
2. Asymptotic model validated by numerical simulation
3. I⁻ vacancies are the most convincing candidate for the main mobile ion species
4. Assuming linear hole-dependent recombination in the bulk and at the TiO₂ interface yields a good fit to measurement

Asymptotic approximation

Mean ion density $N_0 \sim 10^{19} \text{ cm}^{-3}$ [1], making problem too stiff for numerics. However, if the density of ions is that large, it can be assumed that all of the charge accumulates in small Debye layers, causing significant electrostatic potential jumps V_{\pm} in the Debye layers & constant electric field E_b in the bulk. This neglects the contribution of electrons & holes, which is valid for $V < V_{bi}$.

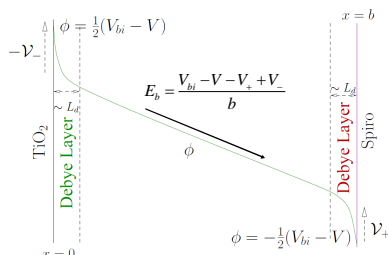

Assuming the main moving ion species to be positively charged I⁺ vacancies [2], the surface charge Q_{\pm} in the Debye layers is given by

$$Q_{\pm} = \pm \sqrt{2q\epsilon N_0 V_T} \left[\exp\left(\frac{V_{\pm}}{V_T}\right) - 1 - \frac{V_{\pm}}{V_T} \right]$$

Figure 1 Simulation domain. The two Debye layers and the bulk form three subdomains.

[1] Aron Walsh *et al.*, *Angewandte Chemie* (2015), Vol. 127, 1811-1814.

[2] C. Eames *et al.*, *Nature Communications* (2015), Vol. 6, 7497.

Testing the asymptotics

To test the asymptotic approximation, a numerical calculation (solid blue lines) was performed for a smaller ion density $N_0 = 10^{17} \text{ cm}^{-3}$, scanning from $V = V_{bi} = 1$ Volt to short circuit then back again. The same calculation was performed with the asymptotic model (dashed green lines).



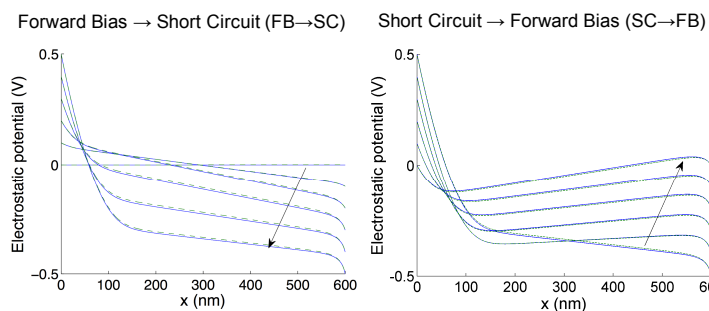


Figure 2 Time evolution of potential in the perovskite film, calculated with a numerical simulation (solid blue lines) and the asymptotic approximation (dashed green lines).

Recombination mechanisms

Monomolecular hole-dependent in bulk only (no surface recombination)

Shockley-Read-Hall recombination in bulk only (no surface recombination)

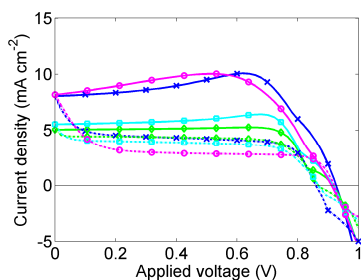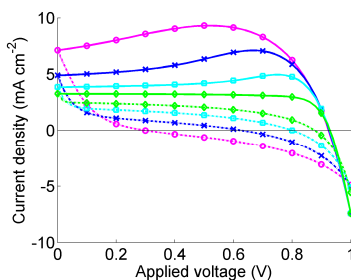

Monomolecular hole-dependent in bulk and at TiO₂-perovskite interface

Measurement

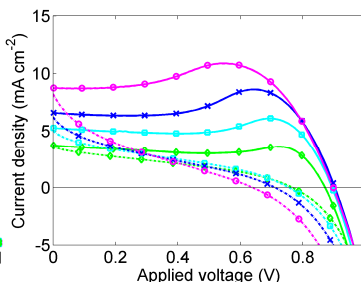
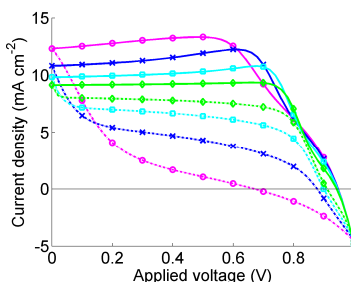


Figure 3 Calculated current-voltage curves for three recombination mechanisms, with a set of measured curves for comparison. Scan rates are 1 V/s (magenta circles), 500 mV/s (blue crosses), 250 mV/s (cyan squares) and 100 mV/s (green diamonds). Solid lines denote FB to SC scans; broken lines denote SC to FB scans.



Nature of the moving ions

Positive ions (e.g. I⁺ vacancies)

Negative ions (e.g. I⁻ interstitials)

$$Q_{\pm} = \pm \sqrt{2q\epsilon N_0 V_T} \left[\exp\left(\frac{V_{\pm}}{V_T}\right) - 1 - \frac{V_{\pm}}{V_T} \right]$$

$$Q_{\pm} = \mp \sqrt{2q\epsilon N_0 V_T} \left[\exp\left(-\frac{V_{\pm}}{V_T}\right) - 1 + \frac{V_{\pm}}{V_T} \right]$$

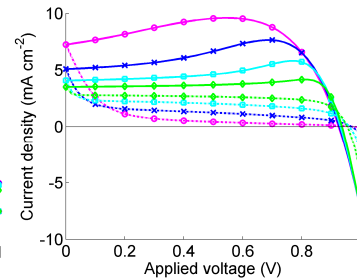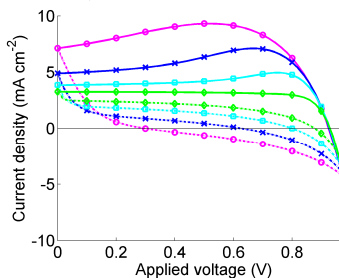

Symmetric ions $Q_{\pm} = 2\sqrt{2} \sinh\left(\frac{1}{2}V_{\pm}\right)$

Measurement

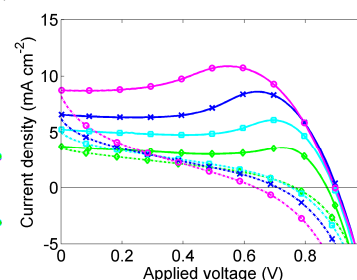
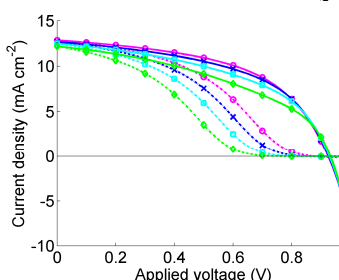


Figure 4 Calculated current-voltage curves for three types of mobile ion system, with a set of measured curves for comparison. Scan rates as in Figure 3. A diffusion coefficient of $10^{-11} \text{ cm}^2/\text{s}$ is assumed for all ions. A monomolecular hole-dependent recombination scheme in the bulk was assumed, with no surface recombination.