

*Citation for published version:*

Owen, R, Mattia, D, Plucinski, P & Jones, M 2017, 'Kinetics of CO<sub>2</sub> Hydrogenation to Hydrocarbons over Iron-Silica Catalysts', *ChemPhysChem*, vol. 18, no. 22, 201700422, pp: 3211-3218.  
<https://doi.org/10.1002/cphc.201700422>

*DOI:*

[10.1002/cphc.201700422](https://doi.org/10.1002/cphc.201700422)

*Publication date:*

2017

*Document Version*

Peer reviewed version

[Link to publication](#)

This is the peer reviewed version of the following article: Owen, R. E., Mattia, D., Plucinski, P. and Jones, M. D. (2017), Kinetics of CO<sub>2</sub> Hydrogenation to Hydrocarbons over Iron–Silica Catalysts. *ChemPhysChem*. doi:10.1002/cphc.201700422, which has been published in final form at <https://doi.org/10.1002/cphc.201700422>. This article may be used for non-commercial purposes in accordance with Wiley Terms and Conditions for Self-Archiving.

## University of Bath

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

### Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

# Kinetics of CO<sub>2</sub> Hydrogenation to Hydrocarbons over Iron-Silica Catalysts

Rhodri E. Owen,<sup>[a]</sup> Davide Mattia,<sup>\*[b]</sup> Pawel Plucinski,<sup>\*[b]</sup> and Matthew D. Jones<sup>\*[a]</sup>

**Abstract:** The conversion of CO<sub>2</sub> to hydrocarbons is increasingly seen as a potential alternative source of fuel and chemicals, while at the same time contributing to addressing global warming effects. An understanding of kinetics and mass transfer limitations is vital to both optimise catalyst performance and to scale up the whole process. In this work we report on a systematic investigation of the influence of the different process parameters, including pore size, catalyst support particle diameter, reaction temperature, pressure and reactant flow rate on conversion and selectivity of iron nanoparticle–silica catalysts. The results provided on activation energy and mass transfer limitations represent the basis to fully design a reactor system for the effective catalytic conversion of CO<sub>2</sub> to hydrocarbons.

## Introduction

Hydrocarbons, currently derived from crude oil, represent a vital source of fuel and are important feedstock for many chemical processes. The need to limit further release of carbon dioxide in the atmosphere, though, coupled with challenges to security of supply, push in the direction of developing new methods for the production of hydrocarbon. Amongst these, one which is attracting increasing attention is the hydrogenation of carbon dioxide (CO<sub>2</sub>).<sup>[1, 2]</sup> The utilisation of an inexpensive and environmentally harmful waste product such as CO<sub>2</sub> is attractive as it can not only produce useful products but also help to aid the reduction of atmospheric CO<sub>2</sub> release. Studies both into the environmental<sup>[3]</sup> and economic<sup>[4, 5]</sup> feasibility of this process have been undertaken and show that while not currently viable, the process holds much promise and research into the area should “not be delayed”.<sup>[5]</sup>

The hydrogenation of CO<sub>2</sub>, could also serve to address one of the main challenges of renewable power generation, the intermittency of supply with no real control over how much power is produced and when. The conversion of CO<sub>2</sub> to hydrocarbons is a potential solution to this problem as it allows any excess energy produced to be converted to a stable chemical energy vector with an established demand and distribution system already in place. The electrochemical splitting of water can be used to produce

renewable hydrogen for the process.<sup>[6]</sup> The use of hydrogen to produce hydrocarbons would also allow to overcome challenges associated with the storage of H<sub>2</sub> as a gas (e.g. leaks, relatively low energy density).

The conversion of CO<sub>2</sub> to hydrocarbons can potentially be achieved through a number of routes, e.g. the conversion of CO<sub>2</sub> to methanol followed by the methanol to gasoline (MTG) process over a zeolite catalyst.<sup>[7, 8]</sup> This paper, however, focuses on the combination of the reverse water-gas shift reaction (RWGS) and the Fischer-Tropsch (FT) process, a route which has attracted a great deal of attention in the literature.<sup>[2, 9-16]</sup>

The majority of studies in the area, though, have focused on ‘traditional’ Fischer-Tropsch catalysts with iron and cobalt-based systems representing a significant portion of the work.<sup>[1, 2]</sup> Generally, cobalt based catalysts give a high selectivity to methane, most likely due to their poor water-gas shift activity.<sup>[17]</sup> While recent studies have indicated that promoted cobalt systems can be effectively used for the formation of hydrocarbons from CO<sub>2</sub>,<sup>[18]</sup> iron’s inherent water-gas shift activity has resulted in it being the main focus for the formation of C<sub>2+</sub> hydrocarbons.<sup>[1, 10]</sup>

The authors have recently shown that while an iron-silica catalyst has relatively low activity with selectivity primarily to methane, the addition of promoters can shift selectivity towards lower (C<sub>2</sub>-C<sub>4</sub>) olefins over 40%.<sup>[19]</sup> While these results are promising, a detailed understanding of the kinetics and mass transfer limitations of this process is vital to both optimise catalyst performance and model or scale up the overall process. Due to the vast industrial interest shown in both the FT and WGS reactions a great deal of attention has been paid to both.<sup>[20-25]</sup> Despite the significant interest in the WGS reaction, kinetic studies of the RWGS reaction have so far remain limited.<sup>[26]</sup> Kinetic studies for the overall process of CO<sub>2</sub> hydrogenation to hydrocarbons has attracted even less attention with very few studies published.<sup>[27, 28]</sup> In this paper, we report on a detailed kinetic analysis of the direct conversion of CO<sub>2</sub> to hydrocarbons using an iron-silica catalyst under realistic process conditions.

## Results and Discussion

### Silica Support Effects

The properties of the support can have a significant influence on the performance of a catalyst both in terms of activity and selectivity.<sup>[29, 30]</sup> Not only can pore diameter influence the size of the supported metal nanoparticles<sup>[31]</sup> but it can also influence the mass transfer properties of the catalyst. In order to determine the influence of these properties on iron-silica catalysts for the hydrogenation of CO<sub>2</sub> a range of catalyst systems were prepared on various silica supports. The specific surface areas (BET) of each of the silica supports and the prepared catalysts are given in Table 1. Generally, as the pore size of the silica support is increased, a decrease in surface area is observed with the catalyst system supported on the SiO<sub>2</sub>-500 support showing the

[a] Dr M.D. Jones, Dr R.E. Owen  
Department of Chemistry  
University of Bath  
Claverton Down, Bath, BA27AY, UK  
E-mail: [m.jones2@bath.ac.uk](mailto:m.jones2@bath.ac.uk)

[b] Prof. D. Mattia, Dr P. Plucinski,  
Department of Chemical Engineering  
University of Bath  
Claverton Down, Bath, BA27AY, UK  
E-mail: [d.mattia@bath.ac.uk](mailto:d.mattia@bath.ac.uk)

Supporting information for this article is given via a link at the end of the document.


lowest surface area (Entry 3). Only a small difference in area is recorded for catalysts supported on silica with different particle sizes with both systems supported on 60 Å pore size silica showing similar surface areas despite significantly different silica particle sizes (Entries 1 and 5).

**Table 1.** Physical properties of prepared catalysts: Reported surface area of SiO<sub>2</sub> supports (S<sub>A</sub>); BET surface area of calcined catalyst (BET); average pore diameter for silica support (d<sub>p</sub>); average metal catalyst particle size (d<sub>m</sub>).

Entry	Catalyst <sup>[a]</sup>	S <sub>A</sub> <sup>[b]</sup>	BET	d <sub>p</sub>	d <sub>m</sub>
		m <sup>2</sup> g <sup>-1</sup>		Å	nm
1	20wt%Fe/SiO <sub>2</sub> -60 <sub>a</sub>	550	372	60	4±1
2	20wt%Fe/SiO <sub>2</sub> -250 <sub>a</sub>	285	216	250	53±19
3	20wt%Fe/SiO <sub>2</sub> -500 <sub>a</sub>	80	82	500	n.d.
4	20wt%Fe/SiO <sub>2</sub> -60 <sub>c</sub>	525	397	60	5±2
5	20wt%Fe/SiO <sub>2</sub> -150 <sub>b</sub>	300	223	150	9±3

[a] Catalysts are supported on SiO<sub>2</sub>-X, where X represents the silica pore size in angstroms (d<sub>p</sub>). A subscript *a* following X is used to denote a silica with a particle size in the range 35-70 μm; a subscript *b* is used to denote a silica with a particle size in the range 250-500 μm; and a subscript *c* indicates a silica particle size of 1000-2000 μm. [b] Surface area as reported by the manufacturer Davisil. n.d. not detectable

Fig. 1 shows representative TEM micrographs for each of the catalyst systems prepared. Whereas large nanoparticles are visible when SiO<sub>2</sub>-250<sub>a</sub> is utilised (Fig. 1 b) each of the other supports show significantly smaller particles with none clearly visible in the SiO<sub>2</sub>-500<sub>a</sub> supported system (Fig. 1 c). Little change is observed with an increase in silica particle size from 35-70 μm (Fig. 1 a) to 1000-2000 μm (Fig. 1 e). The average iron particle size (d<sub>m</sub>) has been determined via statistical image analysis of TEM micrographs and is reported in Table 1.

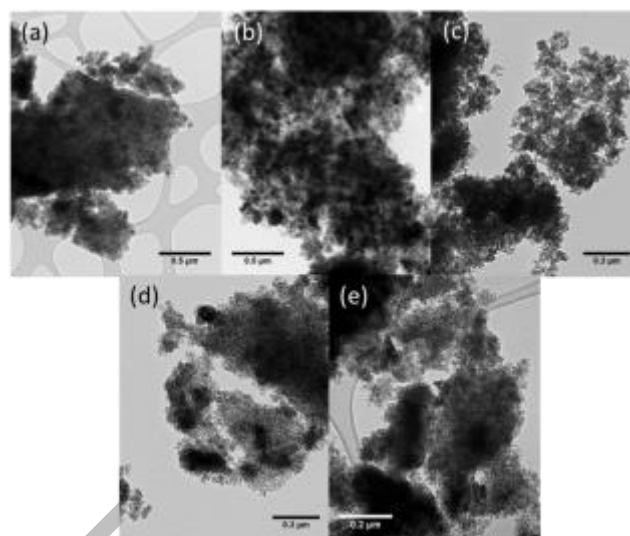

**Figure 1.** Representative TEM micrographs recorded for (a) 20wt%Fe/SiO<sub>2</sub>-60<sub>a</sub> (b) 20wt%Fe/SiO<sub>2</sub>-250<sub>a</sub>, (c) 20wt%Fe/SiO<sub>2</sub>-500<sub>a</sub>, (d) 20wt%Fe/SiO<sub>2</sub>-150<sub>b</sub> and (e) 20wt%Fe/SiO<sub>2</sub>-60<sub>c</sub>.

The data obtained from CO<sub>2</sub> hydrogenation tests conducted on these catalysts are summarised in Table 2. While the size of metal catalyst particles can have a strong effect on reaction performance, the literature shows that this effect becomes significant only for particles sizes below 4 nm.<sup>[32]</sup> As such, it is acceptable to compare catalysts with comparable particle size (entries 1, 2 and 3) and observe that as the pore diameter of the silica increases the CO<sub>2</sub> conversion and selectivity to heavier HCs rises, Fig. 2 a & b. When the CO<sub>2</sub> conversion is compared, the SiO<sub>2</sub>-150<sub>b</sub> (entry 5) does not follow the same trend and is lower than that observed for the smaller particle sizes suggesting possible mass transfer influences. This is further confirmed by the SiO<sub>2</sub>-60<sub>c</sub> (entry 4) catalyst which shows a similar HC selectivity to SiO<sub>2</sub>-60<sub>a</sub> (entry 1) but a lower CO<sub>2</sub> conversion. In order to gain a deeper understanding into these effects further investigations into the role of mass transfer effects were carried out.

**Table 2.** Catalyst test results obtained from 20wt%Fe/SiO<sub>2</sub> catalysts supported on different silica.

Entry	Catalyst <sup>[a]</sup>	Conv. (%)	CO yield (%)	HC yield (%)	Hydrocarbon Distribution						
					C <sub>1</sub>	C <sub>2=</sub>	C <sub>2</sub>	C <sub>3=</sub>	C <sub>3</sub>	C <sub>4</sub>	C <sub>5+</sub>
1	20wt%Fe/SiO <sub>2</sub> -60 <sub>a</sub>	19.0	12.3	6.7	69.4	4.4	16.1	6.4	2.9	0.8	0.0
2	20wt%Fe/SiO <sub>2</sub> -250 <sub>a</sub>	34.8	9.3	25.6	64.5	0.7	22.0	1.8	8.7	2.1	0.2
3	20wt%Fe/SiO <sub>2</sub> -500 <sub>a</sub>	36.1	19.0	17.1	61.5	2.6	21.6	5.4	5.6	2.5	0.8
4	20wt%Fe/SiO <sub>2</sub> -60 <sub>c</sub>	13.6	10.0	3.6	75.1	2.3	15.2	4.4	3.1	0.0	0.0
5	20wt%Fe/SiO <sub>2</sub> -150 <sub>b</sub>	13.8	9.0	4.8	69.5	1.8	19.6	3.8	4.9	0.3	0.0


[a] Catalysts are supported on SiO<sub>2</sub>-X, where X represents the silica pore size in angstroms. A subscript *a* preceding X is used to denote a silica with a particle size in the range 35-70 μm, a subscript *b* is used to denote a silica with a particle size in the range 250-500 μm and a subscript *c* indicates a silica particle size of 1000-2000 μm. All catalyst tests conducted with 0.7 g of catalyst under a 3:1 flow of H<sub>2</sub>:CO<sub>2</sub> (total flow 8 sccm) at atmospheric pressure and at 643 K. WHSV = 0.35 hr<sup>-1</sup>

### Influence of Flow Rate and External Diffusion

The influence of the weight hourly space velocity (WHSV = gas mass flowrate / mass of catalyst) on the performance of the 20wt%Fe/SiO<sub>2</sub>-250<sub>a</sub> catalyst was investigated (Fig. 2 and Table 3). The SiO<sub>2</sub>-250<sub>a</sub> supported system was chosen as it had shown the highest HC yield of the supports tested. As one can see, the influence of WHSV on the average (integral value) rate of CO<sub>2</sub> consumption and hydrocarbons formation (as sum of all hydrocarbons formed during FT synthesis) is very weak. This indicates a very minor influence of the external mass transfer (as a flowrate) on the overall catalytic process. The additional evaluation of the mass transfer effect followed the method developed by Franckaerts and Froment (see Figure S2 in Supporting Information).<sup>[33]</sup> For various experimental conditions, a series of plots of X vs  $m_{\text{cat}}/F_{A0}$  (X= conversion,  $m_{\text{cat}}$ = mass of catalyst,  $F_{A0}$ = CO<sub>2</sub> molar feed rate) have been constructed and the "mass transfer-free" rates of reactions have been determined. The initial slope (for the infinitively high, therefore mass transfer free, flowrate, Eq. 1):

$$\frac{dX}{d\left(\frac{W}{F_{A0}}\right)} \quad \text{Eq.1}$$

corresponded to the reaction rate  $(-r_A) = 9.05 \times 10^{-6} \text{ mol g}_{\text{cat}}^{-1} \text{ s}^{-1}$ . This value has been shown as a dotted line in Fig. 2. Only a slight variation in hydrocarbon distribution is observed by changing the hydrodynamic conditions. This is illustrated by the small variation in chain growth probability observed with increasing WHSV (Fig. 2). This suggests that the influence of external diffusion under these reaction conditions can be neglected. This statement was confirmed by the low value of the Mears criterion,<sup>[34, 35]</sup> ranging from  $2.09 \times 10^{-4}$  to  $2.21 \times 10^{-4}$  (well below the 0.15 threshold, see Eq. S1). The values for the external mass transfer coefficient were calculated using the correlation developed by Gnielinski.<sup>[36]</sup>

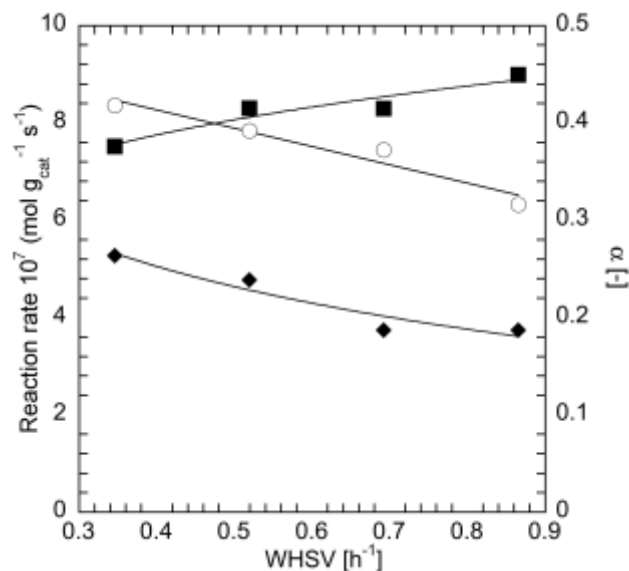

**Figure 2.** Effect of WHSV on the rate of CO<sub>2</sub> consumption (■); HC formation (◆); and chain growth probability (○) for 20wt%Fe/SiO<sub>2</sub>-250<sub>a</sub>. The dotted line corresponds to the 'mass transfer-free' rate of reaction.

Iron-silica catalysts supported on SiO<sub>2</sub>-60<sub>b</sub> were prepared, ground and sieved to give a range of catalyst particle sizes and tested under the same reaction conditions (Table 3, Entries 5-10). There was no significant variation in surface area observed,<sup>†</sup> however, the catalyst systems consisting of larger silica particle sizes did result in slightly high surface areas ( $397 \text{ m}^2\text{g}^{-1}$  vs  $335 \text{ m}^2\text{g}^{-1}$ , for particle sizes  $< 20 \mu\text{m}$  and  $1000\text{-}2000 \mu\text{m}$  respectively).<sup>†</sup> As the catalyst particle size is reduced there is a significant influence on the catalyst performance with smaller catalyst particle diameters generally resulting in increased CO<sub>2</sub> conversion (Table 3, entries 5-10).

For reactions limited by internal diffusion, the concentration of reactant is lower inside each individual particle than at the surface and, as such, the reaction rate in the interior will likely be lower. The decrease in reaction rate inside each particle relative to the rate at the surface can be described by the effectiveness factor,  $\eta$ . The relative ratio of the rate of reaction to the rate of diffusion through each particle can be described by the Thiele modulus,  $\phi$ . If the reaction is diffusion-limited as suggested by the results in Table 3, then the Thiele modulus will be large and for high  $\phi$  values, the approximation  $\eta = 3/\phi$  can be used.<sup>[37]</sup> From this assumption, Eq. 2 can be derived to express the observed rate of reaction (neglecting the influence of the adsorption term and assuming n-th order of the reaction):

$$(-r_A) = \frac{6}{d_p} \sqrt{\frac{D_e}{k_n S_a r_c c_{As}^{n-1}}} k_n S_a r_c c_{As}^n \quad \text{Eq.2}$$


Therefore, according to Equation 2, if the reaction is limited by the internal diffusion (high  $\phi$ ), then the observed rate of CO<sub>2</sub> consumption should be proportional to the inverse of the catalyst particle diameter,  $d_p$ . As such a plot of observed rate against  $1/d_p$  should give a straight line. Fig. 3 shows the resulting plots for the rate of CO<sub>2</sub> consumption and the rates of HC formation (C<sub>1</sub> and C<sub>2</sub> only). The linear relationship observed for these plots indicates that the catalytic process is indeed being limited by the rate of internal diffusion and, as such, catalyst particle size should be kept below  $20 \mu\text{m}$  to obtain optimum catalyst performance. The intercept value for the straight line was not 0 as predicted by Eq. 2. This fact may result from the integral treatment of the reaction rate (average reaction rate was used), especially in the case of CO<sub>2</sub> consumption (high values of conversion). For rates of hydrocarbon formation, with much lower values of the yield of individual reactions, the intercept values were closer to 0. The application of the Langmuir-Hinshelwood type rate equation (with the adsorption terms) should result with similar dependency of the reaction rate on the value of  $d_p^{-1}$ ; resulting in different slopes due to different rate equations.<sup>[38-41]</sup>

As illustrated in Fig. 3 the catalyst particle size also has a large effect on the hydrocarbon distribution. For the two catalyst systems with the smallest particle diameters much higher chain growth probabilities are observed. Once the silica particle size is increased to the  $106\text{-}125 \mu\text{m}$  range, there appears to be little influence on the observed alpha values. This strongly suggests that the internal diffusion is having a large impact on the catalyst performance.

**Table 3.** Catalyst test results obtained from 20wt%Fe/SiO<sub>2</sub>-250<sub>a</sub> at various WHSV (entries 1-4) and 20wt%Fe/SiO<sub>2</sub>-60 (entries 5-10) with various particle diameters.

Entry	WHSV/Catalyst Particle Diameter Range	Conv. (%)	CO yield (%)	HC yield (%)	Hydrocarbon Distribution						
					C <sub>1</sub>	C <sub>2=</sub>	C <sub>2</sub>	C <sub>3=</sub>	C <sub>3</sub>	C <sub>4</sub>	C <sub>5+</sub>
1	0.35 h <sup>-1</sup>	35.4	10.6	24.8	54.7	1.5	20.8	4.1	10.6	7.1	1.2
2	0.52 h <sup>-1</sup>	26.0	11.1	15.0	58.8	2.4	19.5	5.8	7.7	4.7	1.1
3	0.69 h <sup>-1</sup>	19.5	10.7	8.8	63.5	3.2	18.1	6.5	5.3	2.1	1.3
4	0.87 h <sup>-1</sup>	16.9	9.9	7.0	68.2	3.7	15.7	6.0	4.3	2.2	0.0
5	<20 μm	41.9	7.9	34.0	66.3	0.6	19.6	1.1	8.6	2.9	0.9
6	53-75 μm	24.6	9.9	14.7	59.4	2.2	21.4	4.5	8.3	3.2	0.6
7	106-125 μm	15.4	10.2	5.2	69.8	8.5	13.0	7.7	0.9	0.3	0.0
8	180-250 μm	15.0	9.7	5.3	73.6	10.2	8.8	7.4	0.0	0.0	0.0
9	355-500 μm	14.0	9.7	4.3	74.4	10.7	7.1	7.9	0.0	0.0	0.0
10	1000-2000 μm	13.1	9.0	3.3	80.3	11.0	2.8	5.8	0.0	0.1	0.0


[a] All catalyst tests conducted with 0.7 g of catalyst under a 3:1 flow of H<sub>2</sub>:CO<sub>2</sub> at atmospheric pressure and 643 K. Total flow was varied for Entries 1-4, for Entries 5-10 total flow was kept constant at 8 sccm

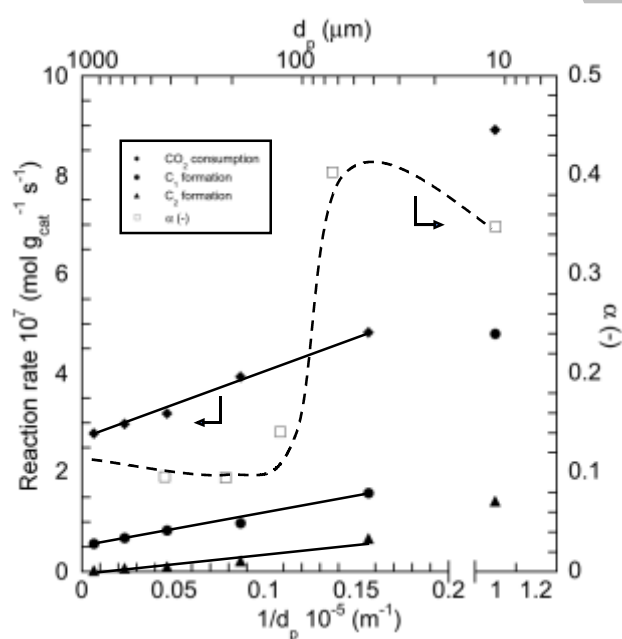

**Figure 3.** Variation of chain growth probability,  $\alpha$ , with increasing support particle size ( $d_p$ ), and correlation between the observed rate of reaction and the inverse of the catalyst particle diameter. All tests conducted with 0.7 g catalyst under 3:1 flow of H<sub>2</sub>:CO<sub>2</sub> at 1 bar, and 643 K.

### Influence of Reaction Temperature

Hydrogenation of CO<sub>2</sub> to HCs is a two-step process; firstly, the endothermic reverse water-gas shift reaction (RWGS), Eq. 3, followed by the exothermic Fischer-Tropsch process, Eq. 4:



Thus, meaning that the reaction temperature can have a significant influence on the overall process both in terms of CO<sub>2</sub> conversion and product selectivity. Studies have shown that temperature effects on the FT process are significant with higher temperatures generally leading to a poorer product distribution with a high methane selectivity.<sup>[24]</sup> With the RWGS reaction being endothermic higher temperatures tend to lead to higher conversions and so in order to obtain a high CO<sub>2</sub> conversion with a low methane selectivity a compromise must be reached.


As the RWGS reaction is reversible, the obtainable CO<sub>2</sub> conversion for a given reaction temperature is determined by the equilibrium position. The calculated equilibrium CO<sub>2</sub> conversion values are illustrated in Fig. 4. In order to determine if this was limiting the CO<sub>2</sub> conversion the 20wt%Fe/SiO<sub>2</sub>-250<sub>a</sub> system was tested over a range of temperatures, the obtained data is shown in Table 4 and in Fig. 4. At lower temperatures (< 280 °C) the observed CO<sub>2</sub> conversion is below the thermodynamically calculated value indicating that the process is not thermodynamically limited at these temperatures. As the temperature increases the CO<sub>2</sub> conversion exceeds the predicted one. This can be explained by the fact that the RWGS reaction is not the only process occurring. The FT process consumes the formed CO and so forces the equilibrium position further to the right. Fig. 4 also shows the equilibrium conversion possible if 90 % of the formed CO is removed.

**Table 4.** Data obtained from catalyst tests utilising 20wt%Fe/SiO<sub>2</sub>-250<sub>a</sub> over a range of temperatures

Entry	Temperature °C	Conv. (%)	CO yield (%)	HC yield (%)	Hydrocarbon Distribution							$\alpha$ -
					C <sub>1</sub>	C <sub>2=</sub>	C <sub>2</sub>	C <sub>3=</sub>	C <sub>3</sub>	C <sub>4</sub>	C <sub>5+</sub>	
1	230	4.1	3.2	0.9	100.0	0.0	0.0	0.0	0.0	0.0	0.0	
2	250	8.5	6.8	1.7	70.1	0.0	13.8	0.0	8.5	3.7	4.1	0.50
3	280	16.2	6.9	9.2	56.9	0.0	18.7	0.0	13.0	5.2	6.1	0.53
4	300	23.8	6.5	17.3	44.1	0.3	23.2	1.2	16.7	8.0	5.9	0.55
5	330	37.2	6.1	31.2	46.0	0.7	21.5	1.8	13.9	6.8	7.0	0.60
6	370	38.3	8.7	29.6	59.5	1.5	22.5	3.2	9.1	3.3	0.9	0.35
7	430	36.4	12.6	23.8	81.2	1.2	14.0	1.1	2.4	0.0	0.0	0.17


[a] All catalyst tests conducted with 0.7 g of catalyst under a 3:1 flow of H<sub>2</sub>:CO<sub>2</sub> (total flow 8 sccm) at atmospheric pressure.

This illustrates a major advantage available for a catalyst system capable of both the RWGS and FT process simultaneously: A higher equilibrium conversion is obtainable at the same temperature when CO is rapidly consumed. At temperatures above 300 °C the CO<sub>2</sub> conversion exceeds equilibrium conversion modelled without CO removal but still remains below the values obtained if a 90 % CO removal is accounted for. This indicates that at these higher temperatures either the reaction is not limited by the equilibrium conversion of the RWGS reaction or less than 90% of the formed CO is being consumed. At reaction temperatures above 300 °C no further increase in CO<sub>2</sub> conversion is observed with the values recorded plateauing.

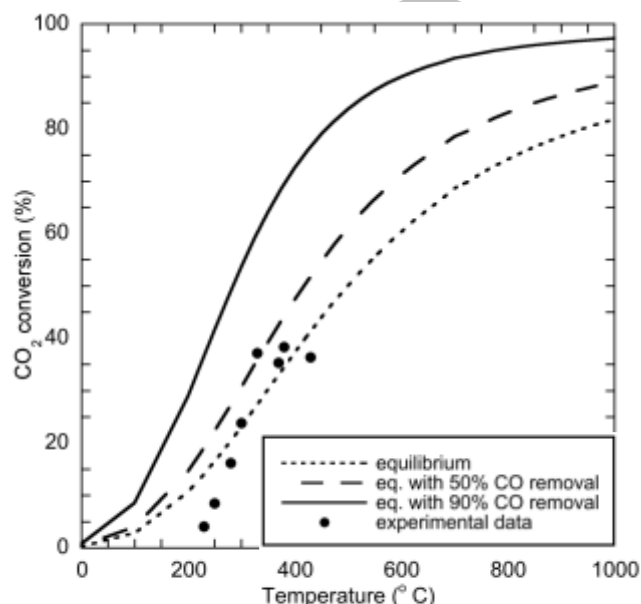

**Figure 4.** Measured CO<sub>2</sub> conversion values resulting from CO<sub>2</sub> hydrogenation over 20wt%Fe/SiO<sub>2</sub>-250<sub>a</sub> (0.70 g catalyst, 3:1 H<sub>2</sub>:CO<sub>2</sub> ratio, total flow 8 sccm). Calculated equilibrium conversion curves shown for comparison.

Fig. 5 shows an Arrhenius plot obtained by plotting the natural logarithm of CO<sub>2</sub> conversion and CH<sub>4</sub> yield against 1/T. At lower temperatures (230-300 °C) the system appears to obey the Arrhenius law with a linear relationship observed. Over this range the slope can be used to calculate the apparent activation energy of the RWGS reaction (from CO<sub>2</sub> conversion) and the activation energy for the conversion of CO<sub>2</sub> to CH<sub>4</sub> (from CH<sub>4</sub> yield) these values are 81.0 kJmol<sup>-1</sup> for CH<sub>4</sub> and 59.3 kJmol<sup>-1</sup> for CO<sub>2</sub> conversion. The value obtained for the RWGS reaction corresponds well with previously reported values.<sup>[27, 42]</sup> At higher temperatures both data sets plateau and no longer follow the behaviour predicted by the Arrhenius equation. The increase of the reaction temperature increases the rate of reaction exponentially (Arrhenius equation) and at high temperatures, the internal diffusion and/or external mass transfer limit the overall catalytic process. Therefore, the overall rate of reaction becomes almost independent of temperature.

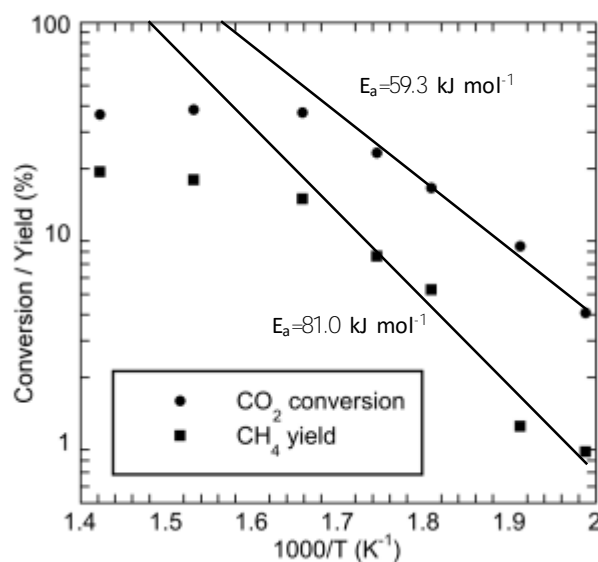


**Figure 5.** Arrhenius plot for 20wt%Fe/SiO<sub>2</sub>-250<sub>a</sub>. Experimental conditions: see Table 4.

Applying the Anderson criterion,<sup>[43]</sup> showed that the RHS of equation S2 was several order of magnitude (8) smaller than the LHS of the equation, indicating that the packed bed is in isothermal conditions.

Product selectivity also shows a strong dependence on temperature (Table 4): At low temperatures, a high selectivity to methane is observed with methane accounting for 100 % of the hydrocarbons formed at 230 °C. As the reaction temperature is increased a steady shift towards C<sub>2+</sub> HCs is observed. This is in contrast to what is generally observed under Fischer-Tropsch conditions where a lower temperature generally results in the formation of longer chained hydrocarbons.<sup>[24]</sup> At a reaction temperature of 330 °C the highest selectivity towards C<sub>2+</sub> HCs is observed (56 %), when increased beyond this value a higher selectivity to methane is detected as observed under FT conditions. This trend in hydrocarbon distribution is further illustrated by the variation of chain growth probability with increasing temperature (Table 4). The high selectivity to methane at low temperatures can likely be accounted for by the poor RWGS activity of the catalyst under these conditions. Only small amounts of CO are being formed which in turn results in a low CO/H<sub>2</sub> ratio which favours the formation of shorter HC moieties due to the more hydrogenating environment.

Fig. 6 illustrates the variation of the rate of formation of the individual hydrocarbon species with the temperature. Whereas the rate of methane formation is observed to increase with increasing temperature the majority of C<sub>2+</sub> hydrocarbons show a maximum. This indicates there is an influence of desorption on the formation of these heavier hydrocarbon species.

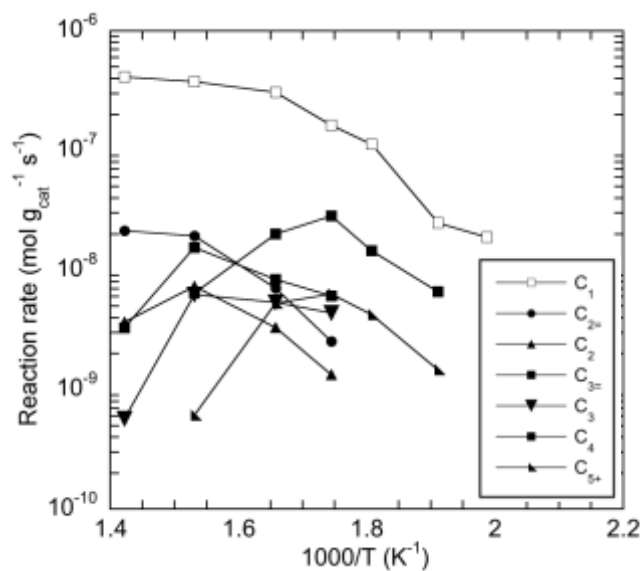


**Figure 6.** The variation in rate of formation of each individual hydrocarbon species with increasing temperature.

#### Influence of Reaction Pressure

Fig. 7a shows the influence of initial CO<sub>2</sub> partial pressure on its conversion. It seems that the partial pressure of CO<sub>2</sub> has no

significant influence on the conversion of carbon dioxide. The small local maximum of conversion for  $p_{CO_2} = 2.75$  bar might be connected with the methanation of formed CO. A similar local maximum has been observed measuring the individual rate of methane formation. As we have a series of consecutive reactions: (i) reverse water gas shift to produce CO, and (ii) methanation of CO, the increase rate of CO consumption in the methanation reaction should shift the equilibrium of the RWGS reaction (see Fig. 4). Additionally, the measured kinetics of CO methanation was interpreted using a Langmuir-Hinshelwood mechanism with a 3<sup>rd</sup> order of adsorption term in the denominator of the rate expression.<sup>[44]</sup> Such a form of the rate expression can be characterised by the local maximum of the reaction rate. The rates of formation of all other species (ethane – heptane) were independent on the initial partial pressure of CO<sub>2</sub> (Fig. 7). This suggests saturation type of the Langmuir-Hinshelwood rate expression. It seems that in all cases the influence of adsorption constants on the rate expression is very strong with plateau existing for  $p_{CO_2} \geq 0.25$  bar.

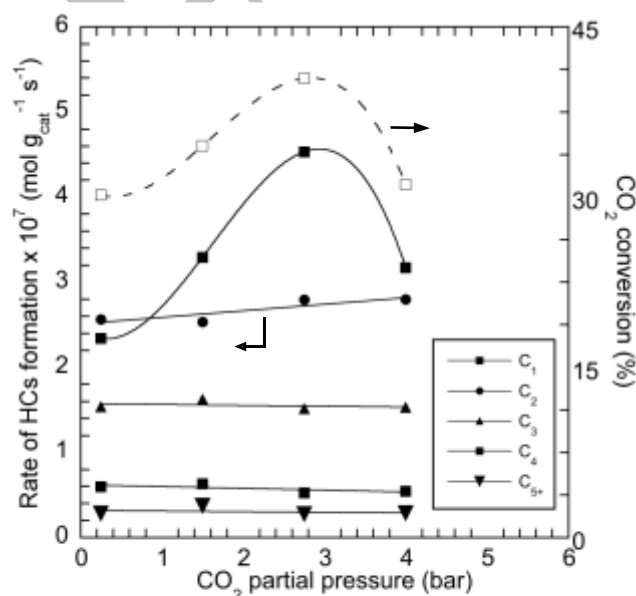

**Figure 7.** The variation in rate of CO<sub>2</sub> consumption and rate of formation of HCs with increasing CO<sub>2</sub> partial pressure.

## Conclusions

This work has shown that properties of the silica support used in an Fe/SiO<sub>2</sub> catalyst for CO<sub>2</sub> hydrogenation can have a large influence on the morphology of the prepared catalyst which likely contributes to the significantly different catalyst performances observed depending on the silica used.

Temperature studies have shown that at lower temperatures the reaction is limited by the rate of the surface reaction. At higher temperatures, however, mass transfer appears to play an important role. Under the conditions tested the external diffusion appears to show little influence on the rate of CO<sub>2</sub> consumption.

The role of internal diffusion appears to play a more important role with a proportional relationship between the inverse catalyst particle diameter and the rate of CO<sub>2</sub> conversion. Evidence for the influence of other factors is also discussed

## Experimental Section

### Catalyst Preparation

Catalysts were prepared using a wet impregnation technique as detailed in our previous work.<sup>[19]</sup> Briefly, the silica was suspended in the minimum amount of methanol. To this a methanolic solution of Fe(NO<sub>3</sub>)<sub>3</sub>·9H<sub>2</sub>O was added to give the a 20wt% loading of iron in the final material. The resulting mixture was stirred for 10 mins and sonicated for 2 hours. The solvent was removed by heating to 65 °C on a rotary evaporator and finally calcined at 450 °C in static air for 16 hours. The preparation method remained constant for all catalyst systems. Silica with various pore diameters and particle sizes were utilised.†

### Catalyst Characterisation

Catalyst morphologies were investigated by TEM using a JEOL 1200 microscope operating at 120 kV. Samples were prepared in ethanol and deposited onto copper or nickel grids. Surface areas were calculated using BET theory with the measurements conducted on a BELSORP-Mini II. Prior to measurements each sample was first degassed at 573 K for 4 hours.

### Catalyst Testing

Catalyst tests were conducted in a purpose-built, tubular, packed-bed, stainless steel reactor. Reactant flow was regulated through the use of mass flow controllers. Typically, 0.70 g of catalyst was packed into the centre of the reactor (130 mm in length, 4.6 mm internal diameter) and held in place with quartz wool. Before each test the catalyst was first reduced at 573.15 K for 2 hours under a stream of pure hydrogen (flow rate = 50 sccm) at 1 bar. Once pre-treatment was complete the reactor was cooled or heated to the desired reaction temperature and a reactant flow of H<sub>2</sub>/CO<sub>2</sub> (3:1) was introduced (total flow 8 sccm) at 1 bar. These values were kept constant throughout all experiments to minimise variability, as the aim of the study was to investigate the kinetics of reaction. The product gases were analysed by gas chromatography on an Agilent 7890A instrument equipped with a TCD, FID and an Agilent 5975C EI mass spectrometer. A HP-PLOT/Q column, 30 m in length, with an internal diameter of 0.530 mm was employed. The percentage hydrocarbon distribution was calculated on a carbon basis as follows; selectivity of hydrocarbon  $x = \text{moles of carbon in hydrocarbon } x / \text{moles of CO}_2 \text{ converted to hydrocarbons}$ .

### Nomenclature

HC = Hydrocarbons  
 $d_p$  = Catalyst particle diameter  
 $r_A$  = Observed rate  
 $r_{AS}$  = Rate at surface  
 $D_e$  = Effective diffusion  
 $k$  = Rate constant  
 $R$  = Catalyst particle radius  
 $S_a$  = Catalyst surface area/mass

$C_{AS}$  = Reactant concentration at surface  
 $\rho$  = Catalyst density  
 $\mu$  = Effectiveness factor  
 $\phi$  = Thiele modulus  
 $P_A$  = Partial pressure of component A  
 $a$  = Adsorption constant for component A  
 $\alpha$  = Chain growth probability  
 $W$  = Catalyst Mass  
 $F$  = Molar flow rate of CO<sub>2</sub>

## Acknowledgements

The EPSRC (EP/H046305) and University of Bath (HEIF) are gratefully acknowledged for funding. All data created during this research are openly available from the University of Bath data archive at <http://dx.doi.org/>

**Keywords:** CO<sub>2</sub> utilisation • Fischer-Topsch • RWGS • Heterogeneous catalysis

- [1] S. Saeidi, N. A. S. Amin, M. R. Rahimpour *J. CO<sub>2</sub> Utilization*. **2014**, *5*, 66-81.
- [2] R. W. Dorner, D. R. Hardy, F. W. Williams, H. D. Willauer *Energ. Environ. Sci.* **2010**, *3*, 884-890.
- [3] O. G. Griffiths, R. E. Owen, J. P. O'Byrne, D. Mattia, M. D. Jones, M. C. McManus *RSC Adv.* **2013**, *3*, 12244-12254.
- [4] Q. Smejkal, U. Rodemerck, E. Wagner, M. Baerns *Chem.-Ing.-Tech.* **2014**, *86*, 679-686.
- [5] G. Centi, G. Iaquaniello, S. Perathoner *ChemSusChem*. **2011**, *4*, 1265-1273.
- [6] R. Abe *J. Photoch. Photobio. C*. **2010**, *11*, 179-209.
- [7] M. Fujiwara, R. Kieffer, H. Ando, Y. Souma *Appl. Catal. A-Gen.* **1995**, *121*, 113-124.
- [8] M. Fujiwara, R. Kieffer, H. Ando, Q. Xu, Y. Souma *Appl. Catal. A-Gen.* **1997**, *154*, 87-101.
- [9] P. Kaiser, R. B. Unde, C. Kern, A. Jess *Chem.-Ing.-Tech.* **2013**, *85*, 489-499.
- [10] P. S. Sai Prasad, J. Bae, K.-W. Jun, K.-W. Lee *Catal Surv Asia*. **2008**, *12*, 170-183.
- [11] G. Centi, E. A. Quadrelli, S. Perathoner *En. Environ. Sci.* **2013**, *6*, 1711-1731.
- [12] R. W. Dorner, D. R. Hardy, F. W. Williams, H. D. Willauer *Catal. Commun.* **2010**, *11*, 816-819.
- [13] R. W. Dorner, D. R. Hardy, F. W. Williams, H. D. Willauer *Energ. Environ. Sci.* **2010**, *3*, 884-890.
- [14] R. W. Dorner, D. R. Hardy, F. W. Williams, H. D. Willauer *Catal. Commun.* **2011**, *15*, 88-92.
- [15] J. P. O'Byrne, R. E. Owen, D. R. Minett, S. I. Pascu, P. Plucinski, M. D. Jones, D. Mattia *Catalysis Science & Technology*. **2013**, *3*, 1202-1207.
- [16] D. Mattia, M. D. Jones, J. P. O'Byrne, O. G. Griffiths, R. E. Owen, E. Sackville, M. C. McManus, P. K. Plucinski *ChemSusChem*. **2015**, *8*, 4064-4072.
- [17] R. W. Dorner, D. R. Hardy, F. W. Williams, B. H. Davis, H. D. Willauer *Energ. Fuel*. **2009**, *23*, 4190-4195.
- [18] R. E. Owen, J. P. O'Byrne, D. Mattia, P. Plucinski, S. I. Pascu, M. D. Jones *Chem. Commun.* **2013**, *49*, 11683-11685.
- [19] R. E. Owen, J. P. O'Byrne, D. Mattia, P. Plucinski, S. I. Pascu, M. D. Jones *ChemPlusChem*. **2013**, *78*, 1536-1544.
- [20] D. C. Grenoble, M. M. Estadt, D. F. Ollis *J. Catal.* **1981**, *67*, 90-102.



- 
- [21]A. N. Pour, M. R. Housaindokht, S. F. Tayyari, J. Zarkesh *J. Nat. Gas Chem.* **2010**, *19*, 362-368.
- [22]A. N. Pour, M. R. Housaindokht, S. F. Tayyari, J. Zarkesh *J. Nat. Gas Chem.* **2010**, *19*, 441-445.
- [23]R. Smith, M. Loganathan, M. S. Shantha *Int. J. Chem. React. Eng.* **2010**, *8*.
- [24]G. P. Van Der Laan, A. A. C. M. Beenackers *Cataly. Rev.* **1999**, *41*, 255-318.
- [25]I. C. Yates, C. N. Satterfield *Energ. Fuel.* **1991**, *5*, 168-173.
- [26]T. Osaki, N. Narita, T. Horiuchi, T. Sugiyama, H. Masuda, K. Suzuki *J. Mol. Catal. -A-Chem.* **1997**, *125*, 63-71.
- [27]T. Riedel, G. Schaub, K. W. Jun, K. W. Lee *Ind. Eng. Chem. Res.* **2001**, *40*, 1355-1363.
- [28]H. D. Willauer, R. Ananth, M. T. Olsen, D. M. Drab, D. R. Hardy, F. W. Williams *J. CO2 Utilization.* **2013**, *3-4*, 56-64.
- [29]D. B. Bukur, X. Lang, D. Mukesh, W. H. Zimmerman, M. P. Rosynek, C. Li *Ind. Eng. Chem. Res.* **1990**, *29*, 1588-1599.
- [30]Ø. Borg, S. Eri, E. A. Blekkan, S. Storsæter, H. Wigum, E. Rytter, A. Holmen *J. Catal.* **2007**, *248*, 89-100.
- [31]A. Y. Khodakov, A. Griboval-Constant, R. Bechara, V. L. Zholobenko *J. Catal.* **2002**, *206*, 230-241.
- [32]H. M. Torres Galvis, J. H. Bitter, T. Davidian, M. Ruitenbeek, A. I. Dugulan, K. P. de Jong *J. Am. Chem. Soc.* **2012**, *134*, 16207-16215.
- [33]J. Franckaerts, G. F. Froment *Chem. Eng. Sci.* **1964**, *19*, 807-818.
- [34]D. E. Mears *Industrial & Engineering Chemistry Process Design and Development.* **1971**, *10*, 541-547.
- [35]D. E. Mears *J. Catal.* **1971**, *20*, 127-131.
- [36]V. Gnielinski *Chemie Ingenieur Technik.* **1980**, *52*, 228-236.
- [37]H. S. Fogler, *Elements of chemical reaction engineering*, Prentice-Hall, **1986**.
- [38]P. Kaiser, F. Poehlmann, A. Jess *Chem. Eng. Technol.* **2014**, *37*, 964-972.
- [39]R. Moene, J. P. Dekker, M. Makkee, J. Schoonman, J. A. Moulijn *J. Electrochem. Soc.* **1994**, *141*, 282-290.
- [40]R. Moene, M. Makkee, J. A. Moulijn *Chem. Eng. J. Bioch. Eng.* **1993**, *53*, 13-24.
- [41]J. O. M. De la Rosa, T. V. Garcia, J. A. O. Tapia *Chem. Eng. Commun.* **1999**, *174*, 53-60.
- [42]J. Kaspar, M. Graziani, A. M. Rahman, A. Trovarelli, E. J. S. Vichi, E. C. da Silva *Appl. Catal. A-Gen.* **1994**, *117*, 125-137.
- [43]R. J. Madon, M. Boudart *Industrial & Engineering Chemistry Fundamentals.* **1982**, *21*, 438-447.
- [44]F. L. Kester in *Hydrogenation of Carbon Dioxide over a Supported Ruthenium Catalyst*, **1974**, [https://web.anl.gov/PCS/acsfuel/preprint%20archive/Files/19\\_1\\_LOS%20ANGELES\\_04-74\\_0146.pdf](https://web.anl.gov/PCS/acsfuel/preprint%20archive/Files/19_1_LOS%20ANGELES_04-74_0146.pdf)
-

---

DRAFT

---