



Citation for published version:

McGuire, TM, Pérale, C, Castaing, R, Kociok-Köhn, G & Buchard, A 2019, 'Divergent Catalytic Strategies for the Cis/Trans Stereoselective Ring-Opening Polymerization of a Dual Cyclic Carbonate/Olefin Monomer', *Journal of the American Chemical Society*, vol. 141, no. 34, pp. 13301-13305. <https://doi.org/10.1021/jacs.9b06259>

DOI:

[10.1021/jacs.9b06259](https://doi.org/10.1021/jacs.9b06259)

Publication date:

2019

Document Version

Publisher's PDF, also known as Version of record

[Link to publication](#)

Publisher Rights

CC BY

University of Bath

Alternative formats

If you require this document in an alternative format, please contact:
openaccess@bath.ac.uk

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Divergent Catalytic Strategies for the *Cis/Trans* Stereoselective Ring-Opening Polymerization of a Dual Cyclic Carbonate/Olefin Monomer

Thomas M. McGuire,[†] Cécile Pérale,[†] Rémi Castaing,[‡] Gabriele Kociok-Köhn,[‡] and Antoine Buchard^{*,†}

[†]Department of Chemistry, University of Bath, Claverton Down BA2 7AY, Bath, U.K.

[‡]Material and Chemical Characterisation Facility (MC²), University of Bath, Bath, U.K.

Supporting Information

ABSTRACT: A dual seven-membered cyclic carbonate/olefin monomer was synthesized from CO₂ and *cis*-1,4-butenediol and polymerized. The properties of the polymer were controlled using divergent catalytic strategies toward the stereochemistry of the olefin. Ring-opening polymerization of the cyclic carbonate using an organocatalytic approach retained the *cis*-stereoconfiguration of the olefin and yielded a hard semicrystalline polymer (T_m 115 °C). Ring-opening metathesis polymerization using Grubbs' catalyst proceeded with high *trans*-stereoregularity (95%) and produced a soft amorphous polymer (T_g -22 °C). *Cis* to *trans* isomerization of the polymer was possible using Cu(I) salts under UV light. In all polymers, the C=C double bond remained available for postpolymerization modification and thermoset resins were formed by cross-linking. From this single monomer, *cis-trans-cis* triblock copolymers, with potential applications as thermoplastic elastomers, were synthesized by combining both strategies using *cis*-1,4-butenediol as a chain transfer agent.

Controlling polymer stereochemistry is a powerful strategy to manipulate its physical properties.^{1–8} The influence of the stereochemistry of alkene bonds in polymer chains is particularly remarkable. In nature, poly(*cis*-isoprene) (natural rubber) has thus vastly superior elastomeric properties compared with poly(*trans*-isoprene) (gutta percha).^{9–11} Catalysis has been an efficient way to control synthetic polymers' stereochemistry by generating chain tacticity, yet examples of its application in *cis/trans* isomerism remain comparatively rare. Hillmyer and co-workers for example demonstrated the stereoselective ring-opening metathesis polymerization of *cis*-cyclooctene monomers using Ru catalysts (*trans*-selective)¹² and Mo catalysts (*cis*-selective).¹³ Becker and Dove reported an organocatalytic stereocontrolled synthesis of unsaturated polyesters, resulting in a tunable *cis/trans* ratio, crystallinity, and mechanical properties.¹⁴ Postpolymerization catalysis was also exploited to isomerize poly(propylene maleate) into poly(propylene fumarate) toward 3D printing and medical applications.^{15–17}

The ability to drastically change polymer properties through *cis/trans* isomerization, e.g. from hard to soft materials, is particularly appealing in the context of synthetic thermoplastics elastomers (TPEs), which have a wide range of applications

including 3D printing, elastomers (e.g., in footwear), pressure-sensitive adhesives, and coatings.^{18,19} TPEs have similar properties to chemically cross-linked rubbers,²⁰ but they can be melt-(re)processed like thermoplastics. TPEs are usually ABA triblock copolymers in which hard/crystalline end-blocks (A) can microphase-separate from the soft/amorphous midblock (B) and act as physical cross-links to strengthen the elastic matrix. To the best of our knowledge, these TPEs are always made from two different monomers and may require purification of the middle block. Motivated by the desire to prepare hard or soft materials, as well as triblock TPEs, from one single monomer and in one pot, we anticipated that *cis/trans* stereoselective polymerization of a selected monomer would provide the desired platform. Here we describe such a monomer, which is a dual cyclic carbonate/olefin. We also demonstrate that these polymers are amenable to cross-linking and thermosets formation.

cis-1,4-Butenediol is a 1,4-diol which may be derived from erythritol,²¹ a fermentation product of glucose (Figure 1). The

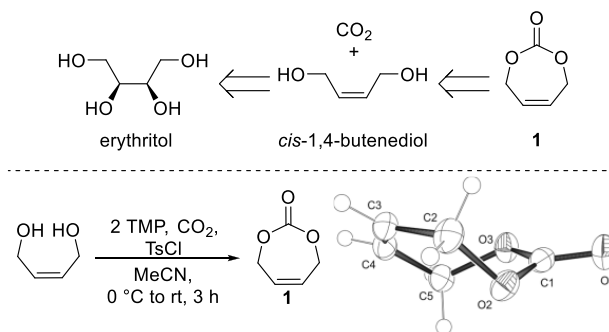


Figure 1. Retrosynthetic approach to 1,4-butenediol from erythritol; synthesis of 4,7-dihydro-1,3-dioxepin-2-one (**1**); ORTEP²³ view of the crystal structure of **1** (displacement ellipsoids at 50% probability level).

corresponding cyclic carbonate, 4,7-dihydro-1,3-dioxepin-2-one (**1**), was readily prepared in one step from CO₂, in 51% crystalline yield, following a procedure reported by our group (Figure 1).²² CO₂ insertion was achieved using 2 equiv of 2,2,6,6-tetramethylpiperidine (TMP) with cyclization facilitated by 1 equiv of *para*-toluenesulfonate chloride (TsCl). **1** is

Received: June 12, 2019

Table 1. Polymerization of **1** Using ROTEP and ROMP Catalysis with Divergent *Cis/Trans* Stereoselectivity^a

entry	[cat.]	[1] ₀ : [cat.] ₀ : [1] ₀ ^b	temp (°C)	time (min) ^c	conv (%) ^d	<i>cis/trans</i> ^e (m:n)	$M_{n,theo}$ ^f (g mol ⁻¹)	$M_{n,NMR}$ ^g (g mol ⁻¹)	$M_{n,SEC} [\mathcal{D}_M]$ ^h (g mol ⁻¹)
1	TBD	50:1:1	22	1	100	100:0	5820	6500	6400 [1.65]
2	TBD	100:1:1	22	10	100	100:0	11 520	10 800	11 000 [1.62]
3	TBD	150:1:1	22	40	100	100:0	17 220	17 100	18 100 [1.53]
4	Sn(Oct) ₂ ⁱ	100:0.5:1	60	10	70 ^j	100:0	8070	9400	8600 [1.16]
5	Sn(Oct) ₂ ⁱ	200:0.5:1	60	18	41 ^j	100:0	9400	7300	8900 [1.27]
7	GII	150:1:0	22	30	100	15:85	17 190	–	22 600 [2.02]
8	GII ^k	150:1:0	22	30	100	5:95	17 190	–	22 500 [1.58]
9	GII	300:1:0	22	50	100	10:90	34 290	–	34 300 [1.80]
10	GII ⁱ	150:1:0	120	30	100	20:80	17 190	–	23 200 [2.69]

^aIn CH₂Cl₂ with [**1**]₀ = 1 mol L⁻¹ unless stated otherwise. ^b**1** is 4-MeBnOH. ^cReaction times not optimized. ^dCalculated by relative integration of the alkene protons in **1** (δ = 5.82 ppm, t (J = 1.8 Hz)) and poly(**1**) (*cis* δ = 5.80 ppm, t (J = 4.1 Hz), *trans* δ = 5.90 ppm, t (J = 3.0 Hz)) in the ¹H NMR spectrum in CDCl₃. ^eDetermined by relative integration of alkene protons in the *trans* and *cis* polymer. ^fCalculated as $M_r(I) + (M_r(I) \times [I]_0 / [I]_0 \times \text{conv}/100\%)$; for ROMP: $M_r(I) = M_r(\text{CHPh})$ and [**1**]₀ = [cat.]₀. ^gFor ROTEP: calculated by the relative integration of the methylene protons in **1** (δ = 5.12 ppm, s) and in poly(**1**); undeterminable for ROMP. ^hCalculated by SEC relative to polystyrene standards in CHCl₃ or THF eluent, $\mathcal{D}_M = M_w/M_n$. ⁱNo solvent. ^jReaction quenched as stirring stopped. ^kReaction carried out under UV light (λ = 365 nm).


a seven-membered cyclic compound with both a carbonate and an alkene functionality, providing opportunities for ring-opening polymerization using metathesis (ROMP) or trans-carbonation (referred to here as ROP) methodologies. We reasoned that ROMP and ROP would both produce a polycarbonate, but could show opposite stereoselectivity toward the configuration of the polymer alkene bonds.

First, various organo- and metal-based catalysts were screened for the ROP of **1** in solution (Table S1). When using 1,5,7-triazabicyclo[4.4.0]dec-5-ene (TBD) as the catalyst (Table 1), ROP proceeded rapidly at room temperature with 100% conversion after 10 min, at a monomer/catalyst/initiator ([**1**]₀: [cat.]₀: [**1**]₀) feed ratio of 100:1:1 (Table 1, entry 2). The quantitative conversion of the monomer to polymer is consistent with the high ring strain of **1** calculated by DFT (Figure S56). For each of the ROP catalysts tested, the *cis* configuration of the monomer's alkene was maintained in the polymer as evidenced by ¹H NMR spectroscopy (Figure 2). Using TBD led to a good correlation between theoretical and experimental M_n values measured by Size-Exclusion Chromatography (SEC), with dispersities (\mathcal{D}_M) of 1.3–1.8 (Tables 1 and S1). ROP could also occur at 60 °C in molten monomer

using Sn(Oct)₂ or TBD as the catalyst (Table 1 entry 4 and Table S1 entry 5, respectively). MALDI-ToF spectrometry and ¹H NMR spectroscopy confirmed the presence of 4-methyl benzyl alcohol and OH chain ends (Figure S27). Initial rate kinetic studies carried out with TBD indicated first-order kinetics ($k_{obs} = 0.117 \text{ s}^{-1}$) with respect to monomer concentration (Figures S30–S31). M_n was found to increase linearly with conversion (Figures S32–S33) with an $M_{n,SEC}$ of 22 100 g mol⁻¹ achievable (degree of polymerization (DP) \approx 200, Figure S18).

Next, the ROMP of **1** was carried out (Scheme 1), catalyzed by Grubbs second generation catalyst (GII). Quantitative

Scheme 1. Divergent Stereoselective Strategies Used for the ROP of **1**

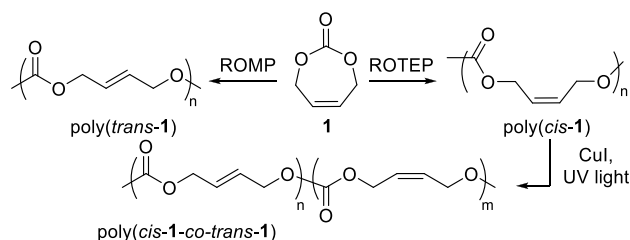

conversion was achieved at 22 °C in solution after 30 min at the [**1**]₀: [GII]₀ 150:1 ratio. Good control over M_n and \mathcal{D}_M was observed across the range of loadings tested (Table 1, entries 7–10 and Table S2). An $M_{n,SEC}$ of up to 34 300 g mol⁻¹ ($DP \approx$ 300) was achieved after 50 min (Table 1, entry 9). Satisfyingly, GII favored the formation of the *trans* isomer with stereoregularities of up to 95% obtainable in 30 min under UV, as observed by ¹H NMR spectroscopy (Figure 2 and Table 1, entry 8). The *trans* selectivity of the reaction was found to be sensitive to time, monomer concentration, and temperature (Table S2). Longer reaction times and high dilution favored formation of the *trans* isomer, with a maximum selectivity of 95% observed after 92 h (Table S2, entry 9). At 120 °C, *trans* selectivity decreased to 88% and 80% when performing reactions in 1,2-tetrachloroethane or neat monomer, respectively (Table S2, entry 6, Table 1, entry 10).

Postpolymerization isomerization was also explored as DFT indicated the *trans* isomer was thermodynamically more stable (Figure S57). Isomerization of the double bond was possible

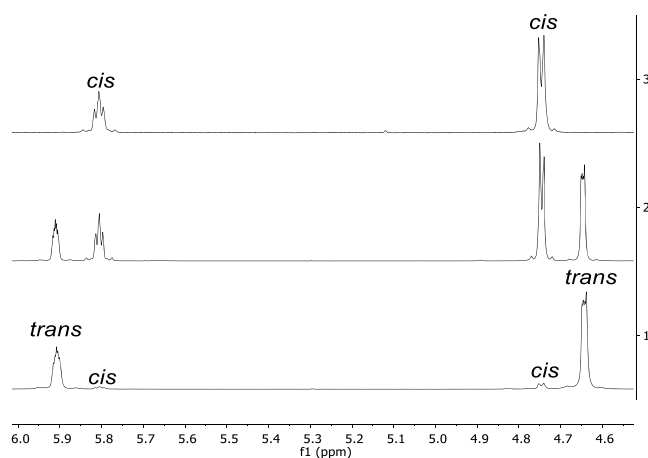


Figure 2. Alkene and methylene regions of the ¹H NMR spectra of poly(**1**), demonstrating the divergence of the catalytic strategies used, and the partial isomerization from poly(*cis*-**1**) (top) to poly(*trans*-**1**) (bottom), using CuI under UV light (middle).

under UV light at room temperature, using 1 alkene equivalent of CuI (52% conversion of poly(*cis*-1) to *trans* isomer, 68 h) (Figure S10). No degradation of the polymer was observed by SEC (Figure S13) or NMR spectroscopy (Figure S12).

The appearance and solubility of poly(*trans*-1) are significantly different from those of poly(*cis*-1). At room temperature poly(*trans*-1) is a viscoelastic solid, soluble in THF, whereas poly(*cis*-1) is a powder, insoluble in THF but soluble in CHCl₃ (Figure S8). Thermogravimetric analysis (TGA) indicated that the onset of thermal degradation ($T_{d,onset}$) for both polymers occurred at 152 °C (Table S4, entries 1 and 2). Differential scanning calorimetry (DSC) revealed for the *cis* polymer the presence of a minor glass transition at -24 °C (T_g) and a melting transition at 115 °C (T_m) (Figure S46). For the 5:95 (*cis/trans*) polymer, a major single T_g at -22 °C was observed, attributed to the *cis* regime (Figure 3 and Figure S47). A T_m was not observed. The

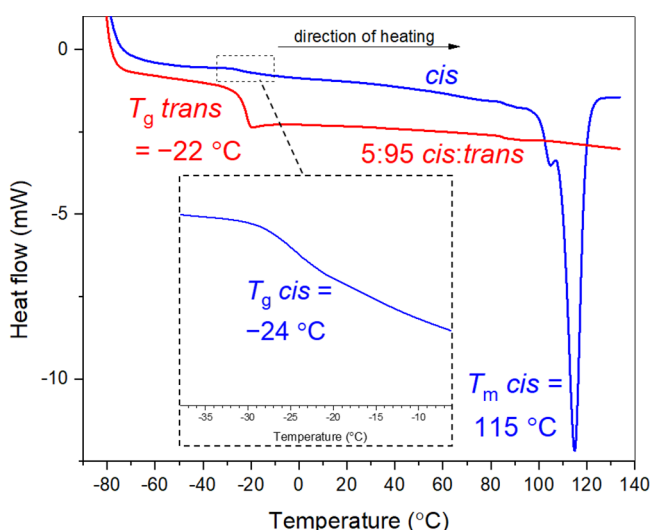



Figure 3. DSC thermograms of poly(*cis*-1) (top) and poly(*trans*-1) (bottom).

significant difference in crystallinity of the *trans* and *cis* polymers highlights the impact of the double-bond isomerism on material properties.

Cross-linking experiments were conducted to explore the potential of the polymers for thermoset formation and coating applications.^{24–26} Trimethylolpropane tris(3-mercaptopropionate) was reacted with poly(*cis*-1) and a *cis/trans* (12:88) polymer in the presence of photoinitiator Irgacure 819 at three alkene/thiol [C=C]₀:[SH]₀ loadings (1:1, 2:1, 5:1). DSC analysis confirmed the formation of highly cross-linked networks with no T_m or T_g being observed up to 140 °C at ratios of 1:1 and 2:1 (Figures S51–S53). Crystallinity was still observed for a weakly cross-linked 5:1 sample (Figure S50). TGA revealed increasing thermal stability with increasing cross-linking (Table S6, maximum $T_{d,onset}$ = 193 °C).

The synthesis of a *cis-trans-cis* triblock was then attempted, utilizing a sequential ROMP/ROTEP concept originally demonstrated by Hillmyer and co-workers,^{27–29} albeit this time with one single monomer, **1** (Scheme 2). *Cis*-butene-1,4-diol was used as a chain transfer agent (CTA) for the ROMP of **1** in a [1]₀:[GII]₀:[CTA]₀ ratio of 20:0.005:1 (Table 2, entry 1). THF was used as the solvent to decrease deactivation of the CTA by GII,³⁰ and a [CTA]₀:[GII]₀ ratio of 200:1 was

Scheme 2. Sequential ROMP/ROTEP Strategy for the Formation of *Cis-Trans-Cis* Triblock Copolymers

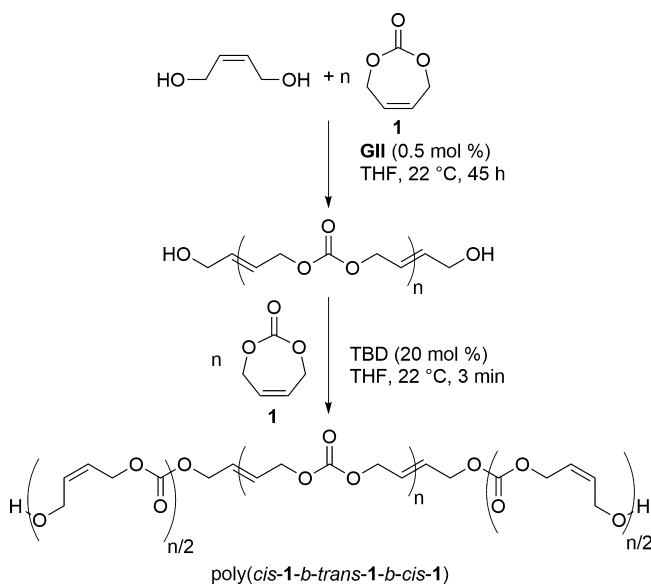

chosen to ensure high incorporation of CTA in the polymer.³¹ After 45 h, an aliquot indicated 100% conversion of **1** to poly(**1**) with a *cis/trans* ratio of 7:93 and an $M_{n,SEC}$ (\bar{M}_n) of 2100 (2.02) g mol⁻¹ (Table 2 entry 1). MALDI-ToF spectrometry revealed the presence of OH chain ends (Figure S31), and ¹H NMR spectroscopy confirmed the incorporation of the CTA into the polymer's backbone with the expected 1:20 ratio (Figure S21). TBD and more monomer were then added in a 2:20 ratio with respect to [CTA]₀. ¹H NMR spectroscopy indicated 100% conversion of monomer after 3 min giving a polymer (ABA-1) with a *cis/trans* content of 54:46 and an $M_{n,SEC}$ (\bar{M}_n) of 4600 (2.06) g mol⁻¹. ¹H DOSY NMR spectroscopy confirmed the presence of only one polymer species, with both *cis* and *trans* regimes, and the sequential increase of molar mass (decrease in diffusion coefficient from 2.06×10^{-8} to 1.48×10^{-8} s⁻¹, Figures S22 and S24). The experiment was repeated at a [1]₀:[GII]₀: [CTA]₀ feed ratio of 40:0.005:1, with additional monomer and TBD (40:1 with respect to [CTA]₀). A *cis-trans-cis* ABA triblock (ABA-2) of higher M_n ($M_{n,SEC}$ = 8900 g mol⁻¹, \bar{D} = 1.60, *cis/trans* 56:44) was obtained (Table 2, entry 2). ¹³C{¹H} NMR spectroscopy gave some insight into the copolymer chain microstructure, revealing limited transcarbonation reactions and well-defined blocks (Figure S25). This was supported by DSC analysis, which showed phase separation and retention of the crystallinity of the *cis* end-blocks (Figure S55).¹⁸

In conclusion, we have demonstrated that from novel dual monomer **1**, divergent stereoselective polymerization catalytic strategies can direct polymer properties between a soft amorphous material (T_g -22 °C) and a hard semicrystalline material (T_m 115 °C). These thermoplastics can further be transformed into thermosets via cross-linking of the alkene polymer backbone. A CTA has also been employed to synthesize triblock ABA polymers from this single monomer, with potential applications as thermoplastic elastomers. Our ongoing efforts are now aimed at investigating the effect of composition and molar mass of these triblock copolymers on nanoscale morphologies and mechanical properties. Finally, the carbonate function of these polymers introduces some

Table 2. Synthesis of Poly(*cis*-1-*b*-*trans*-1-*b*-*cis*-1)

entry	n:CTA	<i>cis/trans</i>	M_{theo} (g mol ⁻¹) ^b	$M_{w,\text{NMR}}$ (g mol ⁻¹) ^c	$M_{n,\text{SEC}}$ ^d (g mol ⁻¹) ^d	\bar{D}_M ^d
1	20:1	54:46 (3:97)	4650 (2370)	3700 (2200)	4600 (2100)	2.06 (2.02)
2	40:1	54:46 (3:97)	9210 (4650)	10 000 (5000)	8900 (4700)	1.60 (1.67)

^aSequential procedure outlined in Scheme 2, with $[1]_0 = 1 \text{ mol L}^{-1}$. Monomer conversion quantitative for each step. Values in brackets were obtained after the ROMP step. ^bCalculated as $M_r(\text{CTA}) + (2 \times n \times M_r(1))$. ^cCalculated by the relative integration of the methylene protons in the CTA ($\delta = 4.19\text{--}4.27 \text{ ppm}$) and the polymer ($\delta = 4.60\text{--}4.80 \text{ ppm}$). ^dCalculated by SEC relative to polystyrene standards in THF eluent.

opportunities for chemical and biological degradation. We anticipate that understanding the degradability of these materials will facilitate their adoption as sustainable alternatives in various commodity and specialty applications.

■ ASSOCIATED CONTENT

📄 Supporting Information

The Supporting Information is available free of charge on the ACS Publications website at DOI: 10.1021/jacs.9b06259.

Experimental and computational procedures, NMR spectra of monomer and polymers, Plot of M_n and \bar{D}_M vs. conversion, polymerization kinetic data, images of SEC traces, MALDI-ToF MS, TGA-MS, DSC traces and DMA data, DFT calculations data and associated digital repository (PDF)

Single-crystal X-ray diffraction data for **1** (CIF)

■ AUTHOR INFORMATION

Corresponding Author

*a.buchard@bath.ac.uk

ORCID

Antoine Buchard: 0000-0003-3417-5194

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

Analytical facilities were provided through the Material and Chemical Characterisation Facility (MC²) at the University of Bath. We thank the University of Bath HPC for computing resources, the UK EPSRC, and the University of Bath (studentship for TMG), as well as the Royal Society (RG/150538, UF/160021 fellowship to AB) for research funding.

■ REFERENCES

- Worch, J. C.; Prydderch, H.; Jimaja, S.; Bexis, P.; Becker, M. L.; Dove, A. P. Stereochemical enhancement of polymer properties. *Nat. Rev. Chem.* **2019**, DOI: 10.1038/s41570-019-0117-z.
- Domski, G. J.; Rose, J. M.; Coates, G. W.; Bolig, A. D.; Brookhart, M. Living alkene polymerization: New methods for the precision synthesis of polyolefins. *Prog. Polym. Sci.* **2007**, *32* (1), 30–92.
- Lu, X. B.; Ren, W. M.; Wu, G. P. CO₂ Copolymers from Epoxides: Catalyst Activity, Product Selectivity, and Stereochemistry Control. *Acc. Chem. Res.* **2012**, *45* (10), 1721–1735.
- Dijkstra, P. J.; Du, H. Z.; Feijen, J. Single site catalysts for stereoselective ring-opening polymerization of lactides. *Polym. Chem.* **2011**, *2* (3), 520–527.
- Carpentier, J.-F. Discrete Metal Catalysts for Stereoselective Ring-Opening Polymerization of Chiral Racemic β -Lactones. *Macromol. Rapid Commun.* **2010**, *31* (19), 1696–1705.
- Miyake, G. M.; Chen, E. Y. X. Synthesis of highly syndiotactic polymers by discrete catalysts or initiators. *Polym. Chem.* **2011**, *2* (11), 2462–2480.
- Stanford, M. J.; Dove, A. P. Stereocontrolled ring-opening polymerisation of lactide. *Chem. Soc. Rev.* **2010**, *39* (2), 486–494.
- Thomas, C. M. Stereocontrolled ring-opening polymerization of cyclic esters: synthesis of new polyester microstructures. *Chem. Soc. Rev.* **2010**, *39* (1), 165–173.
- Bunn, C. W.; B, W. H. Molecular structure and rubber-like elasticity I. The crystal structures of β gutta-percha, rubber and polychloroprene. *Proc. R. Soc. London: Ser. A* **1942**, *180* (980), 40–66.
- Goodman, A.; Schilder, H.; Aldrich, W. The thermomechanical properties of gutta-percha: II. The history and molecular chemistry of gutta-percha. *Oral Surg., Oral Med., Oral Pathol.* **1974**, *37* (6), 954–961.
- Bateman, L. *The Chemistry and Physics of Rubber-Like Substances*; Wiley: New York, 1964.
- Kobayashi, S.; Pitet, L. M.; Hillmyer, M. A. Regio- and Stereoselective Ring-Opening Metathesis Polymerization of 3-Substituted Cyclooctenes. *J. Am. Chem. Soc.* **2011**, *133* (15), 5794–5797.
- Jeong, H.; Kozera, D. J.; Schrock, R. R.; Smith, S. J.; Zhang, J.; Ren, N.; Hillmyer, M. A. Z-Selective Ring-Opening Metathesis Polymerization of 3-Substituted Cyclooctenes by Monoaryloxide Pyrrolide Imido Alkylidene (MAP) Catalysts of Molybdenum and Tungsten. *Organometallics* **2013**, *32* (17), 4843–4850.
- Bell, C. A.; Yu, J. Y.; Barker, I. A.; Truong, V. X.; Cao, Z.; Dobrinyin, A. V.; Becker, M. L.; Dove, A. P. Independent Control of Elastomer Properties through Stereocontrolled Synthesis. *Angew. Chem., Int. Ed.* **2016**, *55* (42), 13076–13080.
- Luo, Y.; Dolder, C. K.; Walker, J. M.; Mishra, R.; Dean, D.; Becker, M. L. Synthesis and Biological Evaluation of Well-Defined Poly(propylene fumarate) Oligomers and Their Use in 3D Printed Scaffolds. *Biomacromolecules* **2016**, *17* (2), 690–697.
- Wilson, J. A.; Luong, D.; Kleinfehn, A. P.; Sallam, S.; Wesdemiotis, C.; Becker, M. L. Magnesium Catalyzed Polymerization of End Functionalized Poly(propylene maleate) and Poly(propylene fumarate) for 3D Printing of Bioactive Scaffolds. *J. Am. Chem. Soc.* **2018**, *140* (1), 277–284.
- DiCiccio, A. M.; Coates, G. W. Ring-Opening Copolymerization of Maleic Anhydride with Epoxides: A Chain-Growth Approach to Unsaturated Polyesters. *J. Am. Chem. Soc.* **2011**, *133* (28), 10724–10727.
- Wang, W.; Lu, W.; Goodwin, A.; Wang, H.; Yin, P.; Kang, N.-G.; Hong, K.; Mays, J. W. Recent advances in thermoplastic elastomers from living polymerizations: Macromolecular architectures and supramolecular chemistry. *Prog. Polym. Sci.* **2019**, *95*, 1–31.
- Drobný, J. G. *Handbook of Thermoplastic Elastomers*, 2nd ed.; William Andrew Publishing: Oxford, 2014.
- Bhowmick, A. K.; Stephens, H. *Handbook of Elastomers*, 2nd ed.; Taylor & Francis: Boca Raton, FL, 2000.
- Raju, S.; Jastrzebski, J.; Lutz, M.; Gebbink, R. Catalytic Deoxydehydration of Diols to Olefins by using a Bulky Cyclopentadiene-based Trioxorhenium Catalyst. *ChemSusChem* **2013**, *6* (9), 1673–1680.
- McGuire, T. M.; Lopez-Vidal, E. M.; Gregory, G. L.; Buchard, A. Synthesis of 5- to 8-membered cyclic carbonates from diols and CO₂: A one-step, atmospheric pressure and ambient temperature procedure. *J. CO₂ Util.* **2018**, *27*, 283–288.
- Farrugia, L. J. WinGX and ORTEP for Windows: an update. *J. Appl. Crystallogr.* **2012**, *45*, 849–854.
- Stöber, T.; Li, C.; Unruangsri, J.; Saini, P. K.; Sablong, R. J.; Meier, M. A. R.; Williams, C. K.; Koning, C. Bio-derived polymers for coating applications: comparing poly(limonene carbonate) and

poly(cyclohexadiene carbonate). *Polym. Chem.* **2017**, *8* (39), 6099–6105.

(25) Koning, C. E.; Sablong, R. J.; Nejad, E. H.; Duchateau, R.; Buijsen, P. Novel coating resins based on polycarbonates and poly(ester-co-carbonate)s made by catalytic chain growth polymerization of epoxides with CO₂ and with anhydride/CO₂. *Prog. Org. Coat.* **2013**, *76* (12), 1704–1711.

(26) Sainz, M. F.; Souto, J. A.; Regentova, D.; Johansson, M. K. G.; Timhagen, S. T.; Irvine, D. J.; Buijsen, P.; Koning, C. E.; Stockman, R. A.; Howdle, S. M. A facile and green route to terpene derived acrylate and methacrylate monomers and simple free radical polymerisation to yield new renewable polymers and coatings. *Polym. Chem.* **2016**, *7* (16), 2882–2887.

(27) Pitet, L. M.; Hillmyer, M. A. Combining Ring-Opening Metathesis Polymerization and Cyclic Ester Ring-Opening Polymerization To Form ABA Triblock Copolymers from 1,5-Cyclooctadiene and d,l-Lactide. *Macromolecules* **2009**, *42* (11), 3674–3680.

(28) Arrington, K. J.; Waugh, J. B.; Radzinski, S. C.; Matson, J. B. Photo- and Biodegradable Thermoplastic Elastomers: Combining Ketone-Containing Polybutadiene with Polylactide Using Ring-Opening Polymerization and Ring-Opening Metathesis Polymerization. *Macromolecules* **2017**, *50* (11), 4180–4187.

(29) Xiang, S.; Zhang, Q.; Zhang, G.; Jiang, W.; Wang, Y.; Zhou, H.; Li, Q.; Tang, J. Facile Synthesis of Block Copolymers by Tandem ROMP and eROP from Esters Precursors. *Biomacromolecules* **2014**, *15* (8), 3112–3118.

(30) Bielawski, C. W.; Scherman, O. A.; Grubbs, R. H. Highly efficient syntheses of acetoxy- and hydroxy-terminated telechelic poly(butadiene)s using ruthenium catalysts containing N-heterocyclic ligands. *Polymer* **2001**, *42* (11), 4939–4945.

(31) Hillmyer, M. A. *The Preparation of Functionalized Polymers by Ring-Opening Metathesis*; California Institute of Technology: 1995.